

TS-1 zeolite as a Lewis acid catalyst for solvent-free one-pot synthesis of 1,3-thiazolidin-4-ones

Published: 21 September 2018

Volume 45, pages 237–247, (2019) [Cite this article](#)

[Download PDF](#)

Access provided by Dr. Babasaheb Ambedkar Marathwada University, Aurangabad



Research on Chemical Intermediates

[Aims and scope](#)

[Submit manuscript](#)

Sachin P. Gadekar & Machhindra K. Lande


425 Accesses 7 Citations [Explore all metrics](#) →

Abstract



Titanium silicate (TS-1) zeolite heterogeneous catalyst is synthesized by the hydrothermally discontinuous method and is characterized by using XRD, SEM, TEM, and NH₃-TPD techniques. The catalytic activity of the TS-1 type zeolite was tested for one-pot solvent-free synthesis of 1,3-thiazolidine-4-ones. The present technique illustrates many benefits, including eco-friendly reaction conditions, environmentally helpful, short response time, simplicity, straightforward separation, catalyst reusability and high yields of the products. Furthermore, the catalyst was utilized for four recycle

reactions and it has been found that the catalyst shows consistent chemical process activity.

Graphical abstract

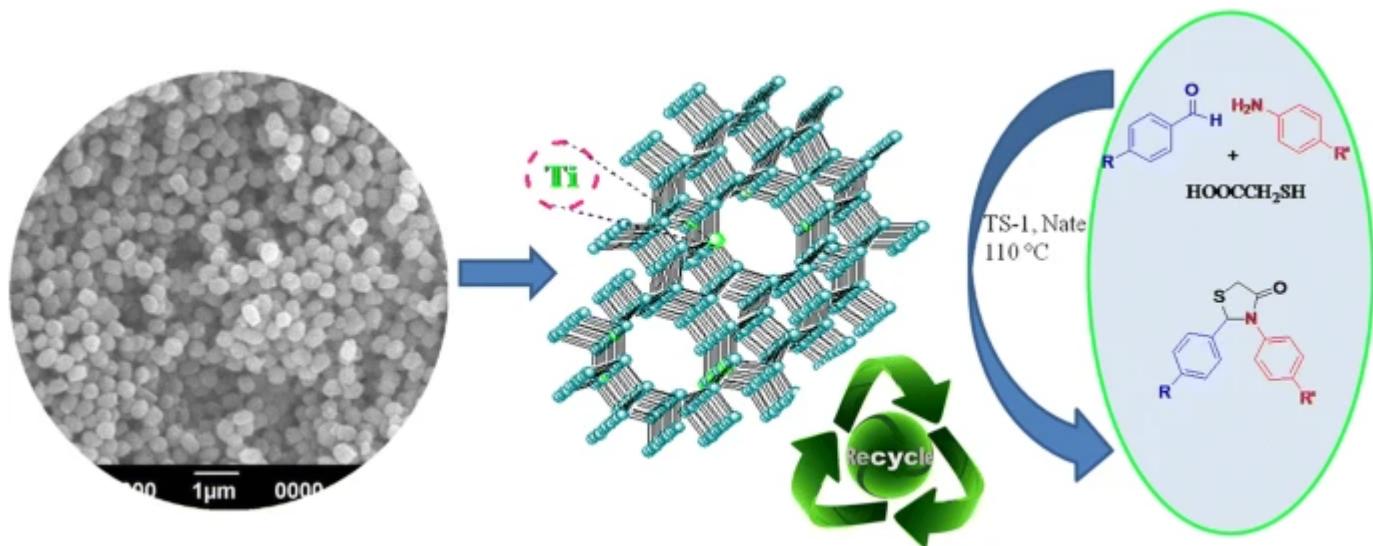


Similar content being viewed by others




A review on zeolite imidazole frameworks: synthesis, properties, and applications

Article | 31 January 2022

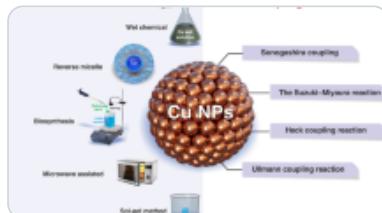

A review on copper-based nanoparticles as a catalyst: synthesis and applications in...

Article | 24 March 2024

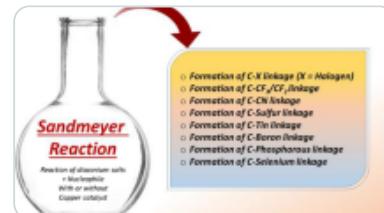

Recent trends in the chemistry of Sandmeyer reaction: a review

Article | 20 August 2021

Use our pre-submission checklist →


Avoid common mistakes on your manuscript.



Introduction

In last 2–3 decades, researchers have had much more interest in the synthesis of heterocyclic (mainly O, N, S, containing) compounds, because of increasing demand of pharmaceutical products, agrochemicals, veterinary products and use of everyday life. Also, they are used in sanitizers, antioxidants, as corrosion inhibitors, as co-polymers, and dyestuff. They are used as catalysts, as well as vehicles in the synthesis of other organic transformation. Some heterocyclic compounds found in natural products, antibiotics (penicillins), alkaloids (morphine), etc. have many applications in heterocyclic moiety [1, 2]. Here, we have synthesized 1,3-thiazolidin-4-ones heterocyclic compounds, which has much more importance in medicinal chemistry (Fig. 1).

Fig. 1

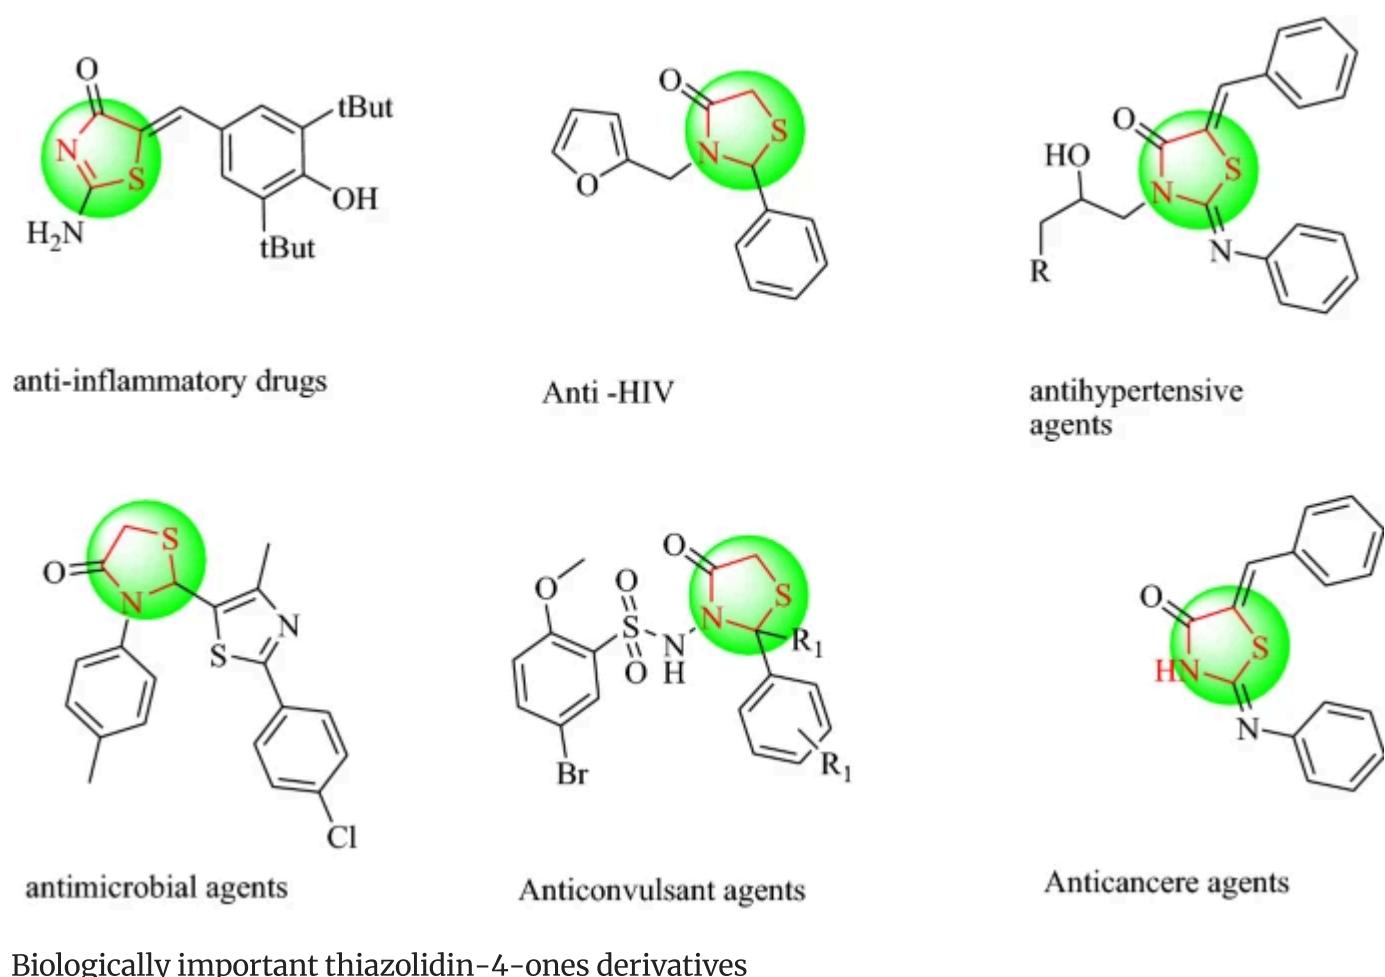

4-Thiazolidinone derivatives are a promising class of heterocycles, which represent a class of chemical products with interesting pharmacological and biological activities such as antidiabetic activity, anticonvulsant, DNA cleavage [3, 4], anti-histaminic [5],

antifungal [6], antihypersensitive [7], anti-infective [8], antitubercular [9], antiviral [10], anti-cancer, antitubercular [11, 12], antimicrobial [13], antioxidant [14], analgesic [15], antiviral, anti-HIV [16, 17], in ibuprofen anti-inflammatory drugs [18, 19], antimicrobial [20, 21]; toxicological 4-thiazolidinone derivatives are genotoxically safe [22].

In a recent trend, one-pot synthesis methodology has taken on a major role in organic transformation attributable to its many benefits including atom economy, high yield property, minimum latency and least by-products as compared to classical artificial methods [23]. Nitrogen, sulfur-containing heterocyclics are the building blocks of natural products and drug molecules; nearly 60% of unique small molecule drugs contain a nitrogen heterocycle [24, 25]. Considering these wide and versatile applications, few catalytic methods have been developed for the synthesis of biologically active 1,3-thiazolidin-4-ones derivatives, such as DIPEA in the presence of toluene 24–36 h, SnCl_2 and acetic acid 14 h [18, 19, 26], nano $\text{Cd-Zr}_4\text{-[PO}_4\text{]}_6$, [24, 25], N -methyl pyridinium tosylate [27], ammonium persulfate [28], ionic liquid [bmim] OH [29], $\text{Bi}[\text{SCH}_2\text{COOH}]_3$ [30] acid catalysed [31] silica supported $\text{Co-Fe}_2\text{O}_4@\text{SiO}_2/\text{PrNH}_2$ [32], $\text{Y}[\text{OTf}]_3$ [33].

Although reported methods are quite efficient, some suffer from one or more types of limitations such as more reaction time, harsh reaction conditions, carcinogenic or hazardous materials, volatile organic/other solvents, homogeneous catalyst separation, low yield and use of an expensive catalyst. Some of the reported catalysts are not reusable and some methods require special conditions, such as microwave or sonication, require high temperature, homogeneous-phase reactions, etc. [29, 34]. Hence, to overcome these limitations, it is necessary to find sustainable, efficient, eco-friendly and cost effective protocols for synthesis of 1,3-thiazolidin-4-ones derivatives. So, we have developed a TS-1 catalyst and firstly reported here a sustainable, eco-friendly, cost effective, efficient protocol for synthesis of 1,3-thiazolidin-4-ones derivatives. It has a heterogeneous solid acid catalyst, as well as strong Lewis and Bronsted acidic properties [35,36,37]. Titanium silicate [TS-1] zeolite is an alternative active heterogeneous Lewis acid catalyst possessing unique properties such as high surface area, high thermal stability, non-toxicity, reusability, and ease of handling, hence is utilized in various industrial processes such as oxidation, epoxidation, alkylation, acylation and cyclic condensation reactions [38,39,40]. In view of the ever increasing importance of green/sustainable synthetic protocol, it was aimed to develop eco-friendly, efficient catalytic methods for organic synthesis.

Experimental

Preparation TS-1

A Lewis acid catalyst, titanium silicate (TS-1), was prepared by using the reported method [41]. Titanium tetrabutoxide ($\text{Ti}[\text{OBu}]_4$) 1.16 mL was mixed in 30 mL of solvent (dry alcohol) and stirred vigorously, Tetraethyl ortho-silicate (TEOS) 24.37 mL and 20% tetrapropyl ammonium hydroxide (TPA-OH) 25 mL was added with vigorous stirring, resulting mixture was stirred for 10 min at 30–35 °C to obtain silica sol. The prepared titanium containing gel was added into the silica sol with constant stirring at 70–75 °C for 60–120 min to remove excess solvent. The final transparent gel maintained basic pH, and was transferred to the autoclave, autogenously pressure at 175 °C for 24 h discontinuously, then treated hydrothermally under static condition. The solid product was filtered, dried at 100 °C for 1 h, and calcined at 500 °C for 4 h under air atmosphere. The subsequent material was normally cooled, portrayed and called Lewis acid catalyst titanium silicate (TS-1).

General procedure for one-pot synthesis of 1,3-thiazolidin-4-ones

A mixture of substituted 4-chloro benzaldehydes (0.140 g, 1 mmol), thioglycolic acid (0.092 g, 1 mmol) and 4-chloro anilines (0.127 g, 1 mmol), 0.05 g of TS-1 catalyst, was magnetically stirred, then gradually the temperature was increased, and refluxed at 110 °C. The progress of the reaction was monitored by TLC using ethyl acetate/ether as a solvent system. The reaction mixture was quenched with crushed ice and extracted with ethyl acetate (3×25 mL). Simultaneously, the catalyst was recovered for next batch reaction. The organic extracts were washed with brine (3×25 mL) and dried over anhydrous sodium sulfate. The solvent was evaporated under reduced pressure to afford the corresponding crude compounds. The obtained crude compounds were recrystallized using ethanol to afford pure products (3a–i).


Results and discussion

In continuation, the synthesised catalyst was characterised by powder X-ray diffraction patterns of TS-1 calcined at 500 °C, as is shown in Figs. 2 and 3, and show intense peaks at $2\theta^\circ = 14.63, 21.81, 22.76, 22.59, 24.04$, and 26.62 with corresponding planes (112), (023),


(150), (511), (250), (004). The planes (150) and (511) indicate the presence of ordered orthorhombic, MFI topology TS-1 framework [42, 43]. The SEM and TEM images suggest that the prepared catalyst has uniform spherical particle size and hexagonal shape with ordered morphology; similarly, they show high acidity, calculated by NH₃-TPD analysis, shown in Table 1. For the synthesised catalyst TS-1, the total acidity (Lewis and Bronsted) is calculated by using the following formula.

$$\text{Acidity} = \frac{\text{Volume of } \text{NH}_3}{\text{Desorbed}} \times 22.4256 \text{ mol/gm}$$

Fig. 2

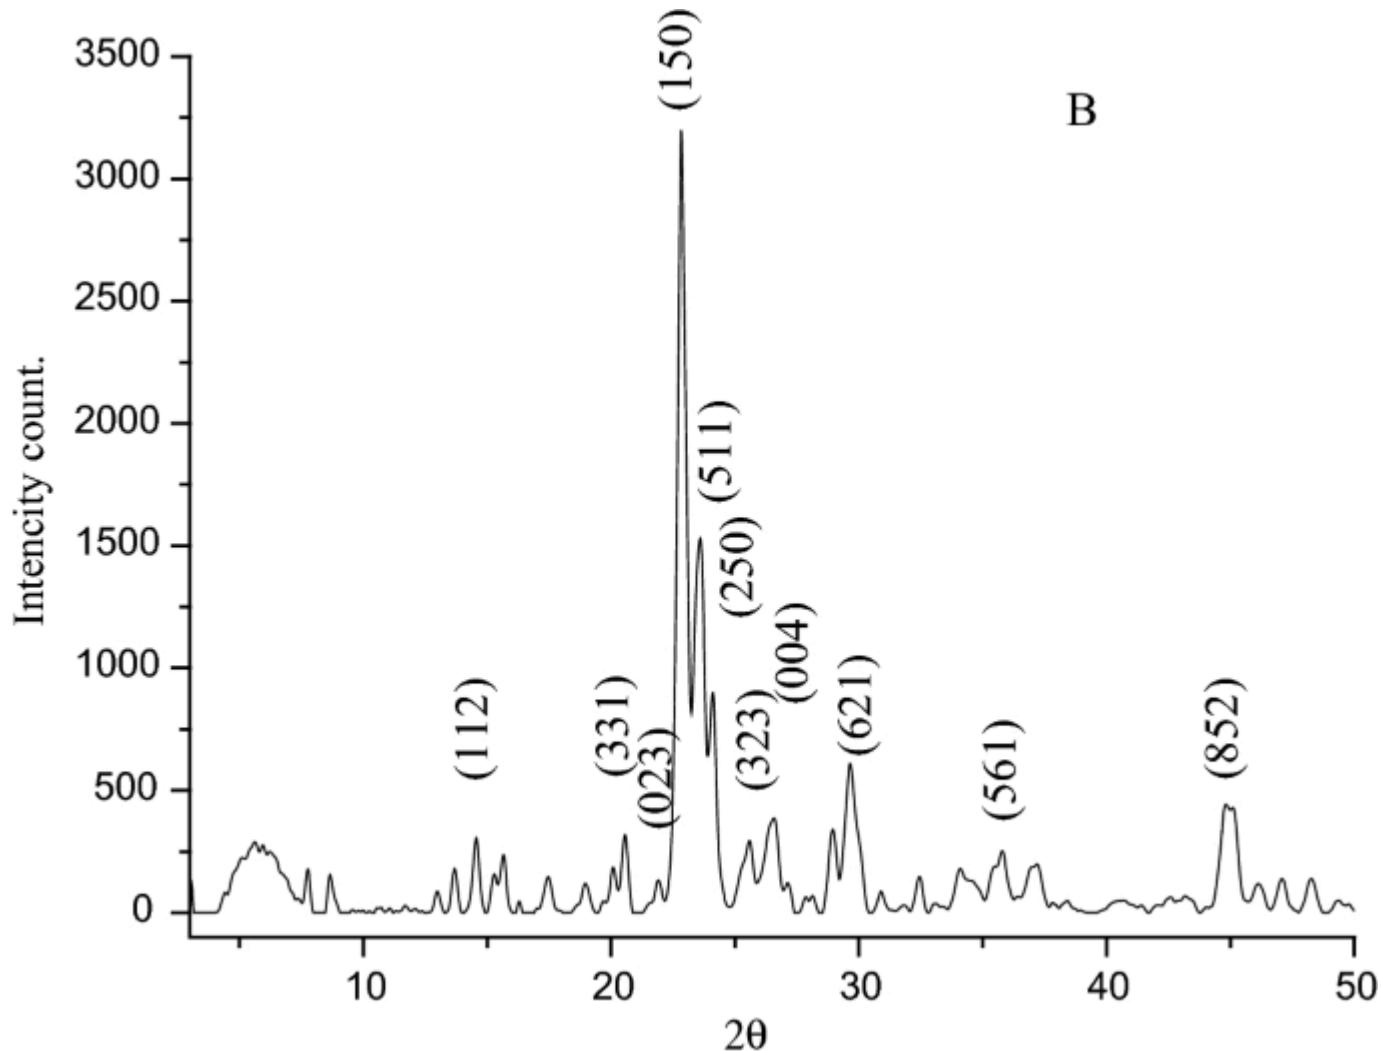

Powder XRD pattern of TS-1 calcined at 500 °C

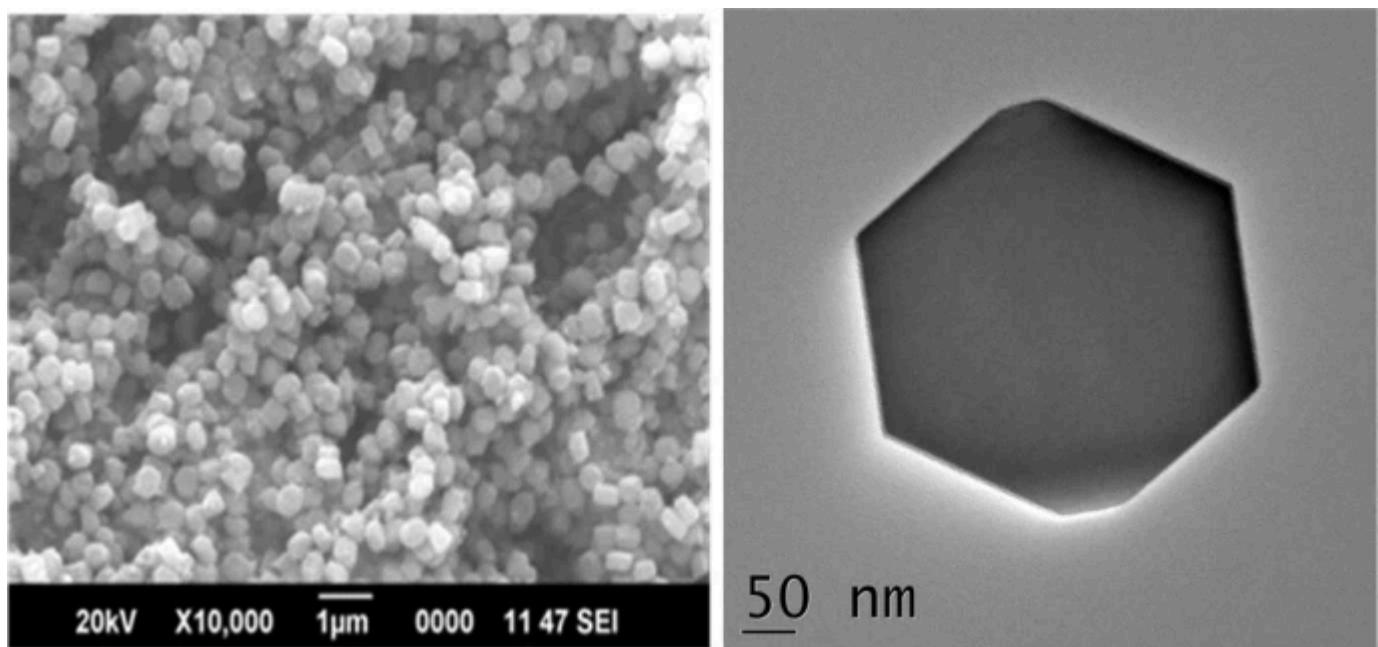Fig. 3

SEM and TEM patterns of TS-1 calcined at 500 °C


Table 1 Total acidity of TS-1 catalyst

Optimization of reaction conditions

In order to find the optimum loading of the catalyst in the reaction of 4-chloro benzaldehydes (1 mmol), thioglycolic acid (1 mmol), 4-chloro anilines (1 mmol), and TS-1 catalyst, initially, many protic and aprotic solvents and acceptable times were screened with loading calcined TS-1 catalyst reflux condition, and the results are summarized in Table 2. A model reaction (**3b**) has completely different quantity of calcined TS-1 catalyst screened with reflux condition and the results are summarized in Table 3. In the absence of a catalyst the reaction didn't give satisfactory results of the specified product (**3b**) within the stipulated time. However, reaction yields were found more in solvent-free conditions as compared to other solvents. It has been found that refluxing the reaction mixture at 110 °C for 10–30 min with loading 0.05 g of TS-1 is an appropriate reaction condition for the synthesis of 1,3-thiazolidin-4-ones derivatives.

Table 2 Effect of various solvents in the synthesis of 3b**Table 3 Effect of the amount of TS-1 on modal reaction 3b**

In order to explore the scope and importance of the present method, under optimized conditions, electronically diverse TS-1 catalyst was tested for the synthesis 1,3-thiazolidin-4-ones derivatives, and the results are summarized in Table 4. It was found that substituted aryl aldehyde and substituted aniline with electron donating and withdrawing groups. It was found that the electron withdrawing groups give maximum yield as compared to the electron donating groups. After optimizing reaction conditions, efforts have been made towards the recovery and reusability of the catalyst (Scheme 1).

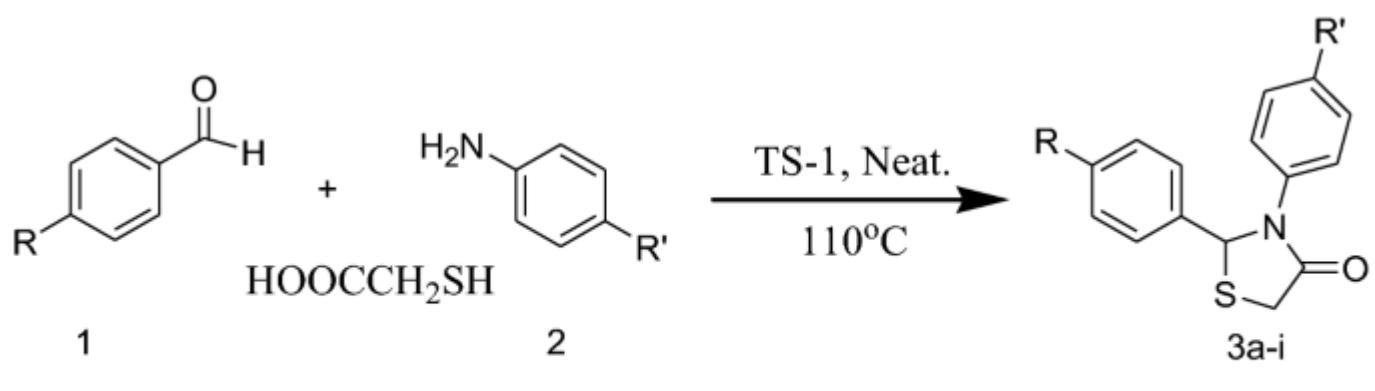
Table 4 TS-1 catalyzed synthesis of 1,3-thiazolidin-4-ones derivatives**Scheme 1**

$R = H, Cl, Me, OMe, NO_2$
 $R' = H, Cl, OMe, NO_2$

The synthetic pathway of compounds 3a–i

The plausible reaction mechanism for the formation of 1,3-thiazolidin-4-ones has been depicted in Fig. 4. (I) A more reactive lone pair of RCHO interacts with Lewis acid catalyst to enhance electrophilicity and nucleophile RNH₂ interacts immediately. Simultaneously, the catalyst acts as a Bronsted base and accelerates the reaction to form a carbon–nitrogen bond (C=N) (III). Respectively, the catalyst again acts as a Lewis acid to interact (III) and enhance electrophilicity (C=N). The thioglycolic acid –SH group acts as nucleophile. Simultaneously, the catalyst acts as a Bronsted base to accelerate reaction forward (IV) of intermediates, then rearranges and cyclization and dehydration give compounds (V), target molecule 1,3-thiazolidin-4-ones (3a–i).

Fig. 4

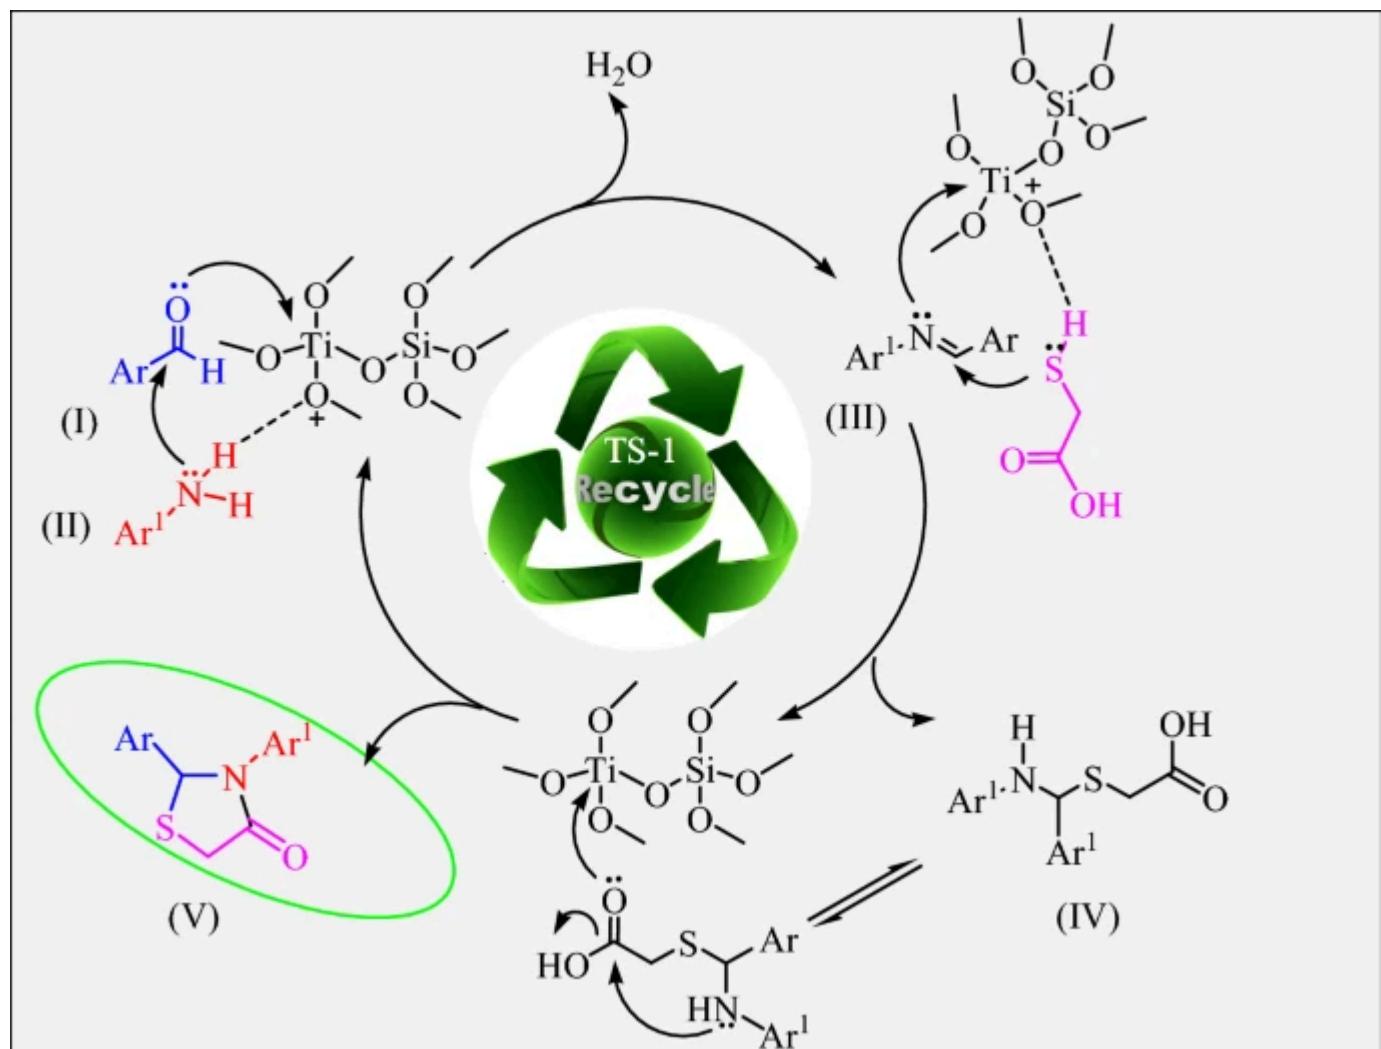


Proposed reaction mechanism of 1,3-thiazolidin-4-ones in the presence TS-1 catalyst

Catalyst activation and reusability

Catalysts were insoluble in solvent; therefore, easy to separate and recover by filtration. After completion of the reaction, catalysts were washed with acetone or any polar solvent to collect the catalyst, which was then dried at 105 °C under vacuum for 10 min. Reusability of the catalyst was also investigated for four successive reaction of model reaction and found that the catalyst has retained almost consistent activity. The catalyst was recycled (**3b** modal reaction) for four cycles without loss of catalytic activity (Fig. 5).

Fig. 5

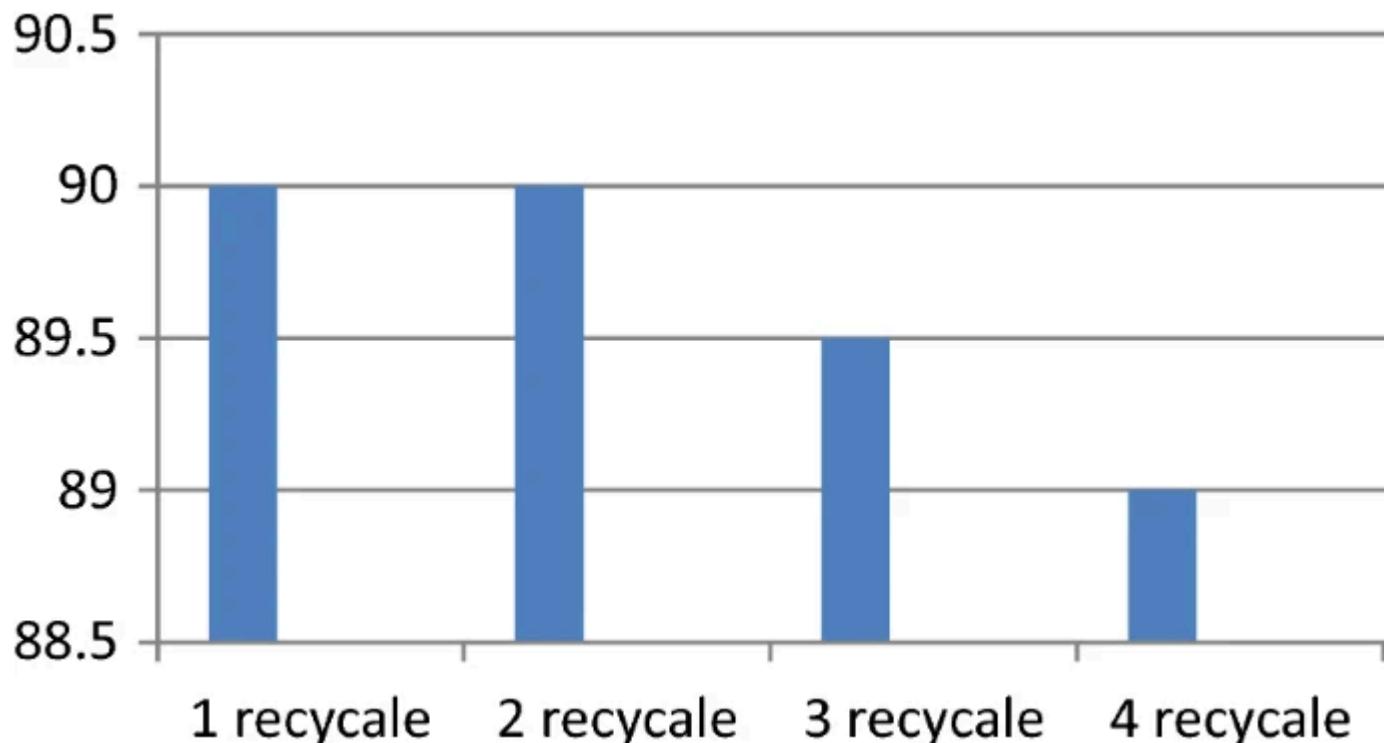

Reusability test of TS-1 for synthesis of **3b**

To specify the benefits of planned methodology, results of various reported strategies are compared with our results and are summarized in (Table 5). It was found that the TS-1 catalyst promotes reaction more effectively than different reported methodologies.

Table 5 Catalytic performance of different reported catalysts for synthesis of 3b

Conclusion

In the present study, synthesized Lewis acid catalyst TS-1 zeolite has highly Lewis and Bronsted acidic sides and excellent catalytic properties. Its catalytic potency was tested in one-pot solvent-free synthesis of 1,3-thiazolidin-4-ones via cyclic condensation of various aldehydes, aniline and thioglycolic acid. The present method offers remarkable advantages over reported methods such as the reusable nature of TS-1, non-toxicity, non-corrosive nature and excellent yield of 1,3-thiazolidin-4-ones, which makes the reaction more successful under environmental benign conditions.

References

1. A. Pragi, A. Varun, H.S. Lamba, D. Wadhwa, IJPSR **3**(09), 2947 (2012)

[Google Scholar](#)

2. H. Bhatt, S. Sharma, Arab. J. Chem. **10**, S531 (2017)

[Article](#) [CAS](#) [Google Scholar](#)

3. N. Siddiqui, M.F. Arshad, S.A. Khan, W.J. Ahsan, Enzyme Inhib. Med. Chem. **25**(4), 485 (2010)

[Article](#) [CAS](#) [Google Scholar](#)

4. A.K. Jain, A. Vaidya, V. Ravichandran, S.K. Kashaw, R.K. Agrawal, Bioorg. Med. Chem. **20**(11), 3378 (2012)

[Article](#) [CAS](#) [PubMed](#) [Google Scholar](#)

5. A. Verma, S.K. Saraf, Eur. J. Med. Chem. **43**(5), 897 (2008)

[Article](#) [CAS](#) [PubMed](#) [Google Scholar](#)

6. V. Opletalova, J. Dolezel, J. Kunes, V. Buchta, M. Vejssova, M. Kucerova-Chlupacova, Molecules **21**, 1592 (2016)

[Article](#) [CAS](#) [PubMed Central](#) [Google Scholar](#)

7. C.M. Bhalgat, P.V. Darda, K.G. Bothara, S.V. Bhandari, J. Gandhi, B. Ramesh, *Euro. J. Med. Chem.* **76**, 580 (2014)

[Article](#) [CAS](#) [Google Scholar](#)

8. A. Gupta, R. Singh, P.K. Sonar, S.K. Saraf, *Biochem. Res. Int.* **2016**, 8086762 (2016)

[PubMed](#) [PubMed Central](#) [Google Scholar](#)

9. D.D. Subhedar, M.H. Shaikh, M.A. Arkile, A. Yeware, D. Sarkar, B.B. Shingate, *Bioorg. Med. Chem.* **26**, 1704 (2016)

[Article](#) [CAS](#) [Google Scholar](#)

10. G. Cihan-Ostundag, E. Gursoy, L. Naesens, N. Ulusoy-Guzel demirci, G. Capan, *Bioorg. Med. Chem.* **1524**(2), 240 (2016)

[Article](#) [CAS](#) [Google Scholar](#)

11. K. Appalanaidu, R. Kotcherlakota, T.L. Dadmal, V.S. Bollu, R.M. Kumbhare, C.R. Patra, *Bioorg. Med. Chem.* **26**, 5361 (2016)

[Article](#) [CAS](#) [Google Scholar](#)

12. C.D. Dago, C.N. Ambeu, W.K. Coulibaly, Y.A. Békro, J.A. Mamyrbekova-Bekro, R.L. Guével, A. Corlu, J.P. Bazureau, *Chem. Heterocycl. Compd.* **53**(3), 341 (2017)

[Article](#) [CAS](#) [Google Scholar](#)

13. D.N. Pansare, N.A. Mulla, C.D. Pawar, V.R. Shende, D.B. Shinde, *Bioorg. Med. Chem.* **24**, 3569 (2014)

- 14.** A.T. Panzariu, M. Apotrosoaei, I.M. Vasincu, M. Drăgan, S. Constantin, F. Buron, S. Routier, L. Profire, C. Tuchilus, *Chem. Cent. J.* **10**, 6 (2016)

[Article](#) [CAS](#) [PubMed](#) [PubMed Central](#) [Google Scholar](#)

- 15.** S.J. Gilani, S.A. Khan, O. Alam, V. Singh, A. Arora, *J. Serb. Chem. Soc.* **76**(8), 1057 (2011)

[Article](#) [CAS](#) [Google Scholar](#)

- 16.** A. Bielenica, G. Sanna, S. Madeddu, M. Struga, M. Jozwiak, M. Koziol, A.E.G. Sawczenko, A.G. Materek, A. Serra, G. Giliberti, *Chem. Biodrug. Des.* **90**(5), 883 (2017)

[CAS](#) [Google Scholar](#)

- 17.** A. Bielenica, G. Sanna, S. Madeddu, M. Struga, M. Jóźwiak, A.E. Kozioł, A. Sawczenko, I.B. Materek, A. Serra, G. Giliberti, *Chem. Biol. Drug Des.* **92**(1), 1157 (2017)

[Google Scholar](#)

- 18.** I.M. Vasincu, M. Apotrosoaei, A.T. Panzariu, F. Buron, S. Routier, L. Profire, *Molecules* **19**, 15005 (2014)

[Article](#) [CAS](#) [PubMed](#) [PubMed Central](#) [Google Scholar](#)

- 19.** K. Liaras, M. Fesatidou, A. Geronikaki, *Molecules* **23**, 685 (2018)

[Article](#) [CAS](#) [PubMed Central](#) [Google Scholar](#)

20. S.J. Gilani, K. Nagarajan, S.P. Dixit, M. Taleuzzaman, S.A. Khan, Arab. J. Chem. **9**, S1523 (2016)

[Article](#) [CAS](#) [Google Scholar](#)

21. P. Samadhiya, R. Sharma, S.K. Srivastava, S.D. Srivastava, Arab. J. Chem. **7**, 657 (2014)

[Article](#) [CAS](#) [Google Scholar](#)

22. F.T. Tugcu, K. Turhan, M. Karadayi, M. Gulluce, Rom. Biotechnol. Lett. **10**, 1 (2017)

[Google Scholar](#)

23. Y. Hayashi, Chem. Sci. **7**, 866 (2016)

[Article](#) [CAS](#) [PubMed](#) [PubMed Central](#) [Google Scholar](#)

24. P. Martins, J. Jesus, S. Santos, L.R. Raposo, C.R. Rodrigues, P.V. Baptista, A.R. Fernandes, Molecules **20**, 16852 (2015)

[Article](#) [CAS](#) [PubMed](#) [PubMed Central](#) [Google Scholar](#)

25. J.S. Ghomi, M. Navvab, H.S. Alavi, Ultrason. Sonochem. **31**, 102 (2015)

[Article](#) [CAS](#) [Google Scholar](#)

26. M. Apotrosoaei, I.M. Vasincu, M. Dragan, F. Buron, S. Routier, L. Profire, Molecules **19**, 13824 (2014)

[Article](#) [CAS](#) [PubMed](#) [PubMed Central](#) [Google Scholar](#)

27. D. Gautam, P. Gautam, R.P. Chaudhary, Chin. Chem. Lett. **23**, 1221 (2012)

28. S. Ebrahimi, J. Sulfur Chem. **37**(6), 587 (2016)

[CAS](#) [Google Scholar](#)

29. M. Mamaghani, M. Pourranjbar, R.H. Nia, J. Sulfur Chem. **35**(1), 1 (2014)

[Article](#) [CAS](#) [Google Scholar](#)

30. N. Foroughifar, S. Ebrahimi, Chin. Chem. **24**, 389 (2013)

[Article](#) [CAS](#) [Google Scholar](#)

31. N. Sadou, S.A. Bouzroura, R. Nechak, B.N. Kolli, V. Morizur, S.P. Martini, E. Dunach, Polycycl. Aromat. Compd. **36**, 1–11 (2016)

[Article](#) [CAS](#) [Google Scholar](#)

32. J.S. Ghomi, M. Navvab, H.S. Alavi, J. Sulfur Chem. **37**(6), 601 (2016)

[Google Scholar](#)

33. J. Luo, Z. Zhong, H. Ji, J. Chen, J. Zhao, F.J. Zhang, Sulfur Chem. **37**(4), 438 (2016)

[Article](#) [CAS](#) [Google Scholar](#)

34. M. Zhengyue, Mod. Appl. Sci. **5**, 3 (2011)

[Google Scholar](#)

35. Z. Zhuo, L. Wu, L. Wang, Y. Ding, X. Zhang, Y. Liu, M. He, RSC Adv. **4**, 55685 (2014)

[Article](#) [CAS](#) [Google Scholar](#)

36. J. Zhuang, Z. Yan, X. Liu, X. Liu, X. Han, X. Bao, U. Mueller, Cat. Lett. **83**, 1 (2002)

[Article](#) [Google Scholar](#)

37. T. Bucko, J. Hafner, L. Benco, J. Chem. Phys. **120**(21), 10263 (2004)

[Article](#) [CAS](#) [PubMed](#) [Google Scholar](#)

38. D. Serrano, R. Sanz, P. Pizarro, I. Moreno, Chem. Commun. **11**, 1407 (2009)

[Article](#) [CAS](#) [Google Scholar](#)

39. X. Deng, Y. Wang, L. Shen, H. Wu, Y. Liu, M. He, Ind. Eng. Chem. Res. **52**, 1190 (2013)

[Article](#) [CAS](#) [Google Scholar](#)

40. Y. Luo, J. Xiong, C. Pang, G. Li, C. Hu, Catalysts **8**, 49 (2018)

[Article](#) [CAS](#) [Google Scholar](#)

41. S. Gadekar, G. Pawar, R. Magar, M. Lande, Polycycl. Arom. Compd. **1** (2017)

42. M.M. Treacy, J.B. Higgins, *Collection of Simulated XRD Powder Patterns for Zeolites*, 4th edn. (Elsevier, Amsterdam, 2001)

[Google Scholar](#)

43. Y. Xue, Y. Xie, H. Wei, Y. Wen, X. Wang, B. Li, New J. Chem. **38**, 4229 (2014)

[Article](#) [CAS](#) [Google Scholar](#)

44. S.M. Sadeghzadeh, M. Malekzadeh, *J. Mol. Liq.* **202**, 46–51 (2015)

[Article](#) [CAS](#) [Google Scholar](#)

45. A. Bolognese, G. Correale, M. Manfra, A. Lavecchia, E. Novellino, V. Barone, *Org. Biomol. Chem.* **2**, 2809–2813 (2004)

[Article](#) [CAS](#) [PubMed](#) [Google Scholar](#)

46. J. Harindran, *IJRCP* **4**(2), 351 (2014)

[Google Scholar](#)

47. H.X. Pang, Y.H. Hui, K. Fan, X.J. Xing, Y. Wu, J.H. Yang, W. Shi, Z.F. Xie, *Chin. Chem. Lett.* **27**, 335 (2012)

[Article](#) [CAS](#) [Google Scholar](#)

48. D. Kumar, M. Sonawane, B. Pujala, V.K. Jain, S. Bhagat, A.K. Chakraborti, *Green Chem.* **15**, 2872 (2013)

[Article](#) [CAS](#) [Google Scholar](#)

Acknowledgements

We are grateful to the head of the Department of Chemistry, Dr. B.A.M., University, Aurangabad, 431004 (MS), India for providing the laboratory facility. The corresponding author MKL is thankful to UGC New Delhi (INDIA) for providing grant under major research Project Funding No. 43-184/2014 (SR). The authors are thankful to STIC Cochin and SAIF Chandigarh, IIT Madras (Department of Chemistry), CDRI Lucknow characterization facilities.

Author information

Authors and Affiliations

Department of Chemistry, Dr. Babasaheb Ambedkar Marathwada University,
Aurangabad, Maharashtra, 431004, India
Sachin P. Gadekar & Machhindra K. Lande

Corresponding author

Correspondence to [Machhindra K. Lande](#).

Electronic supplementary material

Below is the link to the electronic supplementary material.

[**Supplementary material 1 \(DOCX 4086 kb\)**](#)

Rights and permissions

[Reprints and permissions](#)

About this article

Cite this article

Gadekar, S.P., Lande, M.K. TS-1 zeolite as a Lewis acid catalyst for solvent-free one-pot synthesis of 1,3-thiazolidin-4-ones. *Res Chem Intermed* **45**, 237–247 (2019).

<https://doi.org/10.1007/s11164-018-3599-2>

Received

14 July 2018

Accepted

14 September 2018

Published

21 September 2018

Issue Date

15 February 2019

DOI

<https://doi.org/10.1007/s11164-018-3599-2>

Share this article

Anyone you share the following link with will be able to read this content:

[Get shareable link](#)

Provided by the Springer Nature SharedIt content-sharing initiative

Keywords

[Lewis acid](#)

[Titanium silicate \(TS-1\)](#)

[1,3-Thiazolidin-4-ones](#)

[Zeolite catalyst](#)

[Synthesis](#)