



Green synthesis and characterization of Zinc Oxide_{CAL} using Cicer arietinum leaves for NO₂ gas detection

Dayanand B. Jadhav^a  , Rajendra D. Kokate^b

Show more 

 Share  Cite


<https://doi.org/10.1016/j.matpr.2020.08.601> 

[Get rights and content](#) 

Abstract

In this research work, the nanomaterial Zinc Oxide_{CAL} is prepared using green synthesis method. The plant 'Cicer Arietinum leaves (CAL)' is used for synthesis. The formed crystal Zinc Oxide_{CAL} material achieved size 14 nm using X-RD. The characterization technique FT-IR reported the various bonds in CAL extracts and Zinc Oxide_{CAL} material. The technique Energy Dispersive Spectroscopy (EDX) shows the elements present in the material and also reported the concentration of Zn and O. It also gives the FE-SEM, reported hexagonal and spherical shape with size near about 12 nm to 18 nm using Selected area electron diffraction [SAED]. For the NO₂ gas the temperature response, gas response, sensitivity and repeatability for the element Zinc Oxide_{CAL} studied and reported.

Graphical abstract:

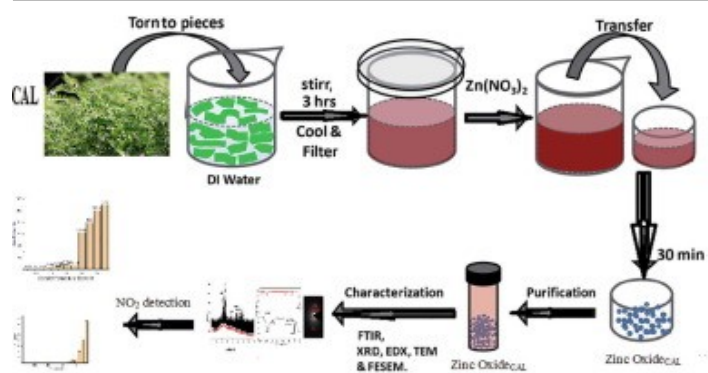

[Download : Download high-res image \(87KB\)](#)

[Download : Download full-size image](#)

Introduction

Nanoscale material have high surface to volume ratio [1], [2], [3], [4]. Synthesis of nanoscale material possible using various methods [5], [6], [7]. Recently focus is on green synthesis [8], [9], [10], [11], [12], [13], [14], [15], [16], [17], [18], [19], [20], [21], [22], [23], [24], [25], [26]. This research work is based on the synthesis of Zinc oxide nanomaterial using young harbhara plant (YHP)/Cicer Arietinum leaves (CAL). From writing records, it is notable that the “(chickpea) Cicer arietinum” locally is known as “chana” in India; [27], [28]. It is a plant ordinarily developed on a farm. Chickpea (Cicer arietinum Leaves) is a green leaves vegetable growing into dry and cool environment [29], [30], [31], [32]. In INDIA, Maharashtra, the plant CAL production occurs in the winter [33], [34]. It has been observed that every single surface of the Cicer Arietinum green leaves plants emits natural acids, which comprise solely of malic $C_4H_6O_5$ and succinic acids $(CH_2)_2(CO_2H)_2$ with a modest quantity of quinic $C_7H_{12}O_6$, citrus $C_6H_8O_7$ (The citrus extract is a frail natural acid. It is a tribasic acid, as it has various bands that respond with base atoms. The structure of CAL plant is anhydrous structure/monohydrate structure. The monohydrate structure can be changed over to the anhydrous structure when it is warmed around temperature of $78^\circ C$. At the point when warmed to temperatures over $175^\circ C$, it breaks down with the loss of CO_2 . Citrus acid promptly frames citrate edifices with metal cations and oxalic acids, answerable for the profoundly acidic nature [35], [36], [37], [38] Fig. 1.

Cicer Arietinum leaves (CAL) are also used as green vegetables. Particularly it can enhance significant dietary supplements. CAL has higher mineral than cabbage leaves/spinach leaves. CAL is prescribed for regions where chickpeas are delivered as nourishment for people. Green acidic medium in the synthesis of Zinc Oxide beginning from promptly accessible dimedone and salicylaldehydes in the nearness of watery medium and at encompassing temperature.

In this research CAL extract is used due to its stability, incorporated zinc oxide nanoparticles characterized using the techniques X-ray diffration (X-RD), scanning electron microscope (SEM)/

EDX and FT-IR. Here, we performed the synthesis of Zinc oxide nanoparticles using CAL extract.

Section snippets

Cicer Arietinum leaves (CAL)

CAL were collected from village Karwandi, Udgir, Dist: Latur, Maharashtra, India. In the winter season farmers takes the production of the Harbhara (CAL). The Zinc nitrate hexahydrate was purchased from Merck Chemical, India Pvt. Ltd. The de-ionized water was utilized all through the response procedure....

Zinc Oxide nanoparticles using CAL

1.5 M , Zn(NO₃)₂·6H₂O taken in 70 mL of filter water and all with a stirrer. The green, fresh CAL water. The CAL extract concentrate of 100 mL combined in Zn(NO₃)₂·6H₂O This mixer is kept at 70 °C in a petry dish and heated consistently until the water disintegrated totally. The acquired antecedent altogether washed with filter water few times. The contaminationless prepared mixer further dried in a broiler at 90 °C. Furthermore, dried mixer calcinated in the air at 170 °C for 3 h to get the...

X-RD

Fig. 2 shows the X-RD of green synthesized Zinc Oxide_{CAL}. As comparing with JCPDS card (Card No.75-0576),The values are $a = 3.249 \text{ \AA}$, $c = 5.176 \text{ \AA}$, $c/a = 1.592 \text{ \AA}$. The values are similler to the hexagonal structure of Zinc Oxide_{CAL} as reported in present standard database. The obtained values of 2θ in degree and hkl (Miller indices) are 31.71° (100), 34.40° (002), 36.22° (101), 47.37° (102), 56.54° (110), 62.69° (103), and 67.87° (112).In the shown Fig. 2 the various difrection peaks were...

Gas sensing characteristics

The Fig. 5. Is the observation of operating temperature on the NO₂ gas. Upto 275 °C the gas response not responded , but after that in the range from 275 °C to 300 °C the gas response value recordrd as 156.88. In the range from 325 °C, 350 °C & 375 °C the resonse value recorded as 199,250.33 & 275 respectively.

It is recorded Zinc Oxide_{CAL} the reaction time is close around 20 to 30 s and the recuperation time is close around 200 to 250 s. Sensitivity of the gas estimated as change in obstruction ...

Conclusions

The synthesis of Zinc Oxide by using Cicer Arietinum leaves (CAL) recorded in the nanoscale. This technique offers environmental friendly approach in the sythesis of Zinc Oxide_{CAL}. The formed ZnO CAL nanoparticles were characterized by X-RD, SEM, FT-IR, and EDX. The nanoscale size and material is confirmed using all these methods. The Gas NO₂ detection charcteristic of Zinc Oxide_{CAL} nanoparticles was estimated at the working temperature 275 °C to 375 °C. In this way we have investigated as Zinc ...

Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper....

Acknowledgements

The authors acknowledge the facilities under the INUP at IIT Bombay. The authors presents sincere gratitude to the Farmers of Karwandi village & Director INUP IIT Bombay Dr. K. Nageshawari....

[Special issue articles](#) [Recommended articles](#)

References (38)

P. Deepak *et al.*

P. Jambunathan *et al.*

[Combining biological and chemical approaches for green synthesis of chemicals](#)

Curr. Opin. Chem. Eng. (2015)

O.V. Kharissova *et al.*

[The greener synthesis of nanoparticles](#)

Trends Biotechnol. (2013)

V.A. Soares

[Green synthesis of Zinc Oxide nanoparticles using whey as an effective chelating agent](#)

Mater. Lett. (2020)

S.P. Dubey *et al.*

[Green synthesis and characterizations of silver and gold nanoparticles using leaf extract of Rosa rugosa](#)

Colloids Surf., A (2010)

H. Bar *et al.*

[Green synthesis of silver nanoparticles using latex of *Jatropha curcas*](#)

Colloids Surf., A (2009)

C.A. Soto-Robles

[Study on the effect of the concentration of *Hibiscus sabdariffa* extract on the green synthesis of Zinc Oxide nanoparticles](#)

Results Phys. (2019)

K.B. Singh

[Chickpea \(*Cicer arietinum* L.\)](#)

Field Crops Research (1997)

G.D. Sáez *et al.*

[Identification and biotechnological characterization of lactic acid bacteria isolated from chickpea sourdough in northwestern Argentina](#)

LWT (2018)

A.K. Kalkan *et al.*

[Electronic and opto-electronic devices fabricated from nanostructured high surface to volume ratio thin films](#)

Google Patents (2008.)



[View more references](#)

Cited by (0)

[View full text](#)

© 2021 Elsevier Ltd. All rights reserved. Selection and peer-review under responsibility of the scientific committee of the International Conference on Materials, Processing & Characterization.



All content on this site: Copyright © 2024 Elsevier B.V., its licensors, and contributors. All rights are reserved, including those for text and data mining, AI training, and similar technologies. For all open access content, the Creative Commons licensing terms apply.

