

[Ferroelectrics](#) >

Volume 584, 2021 - Issue 1

✓ Full access

84 Views | 1 CrossRef citations to date | 0 Altmetric



Research Article

Synthesis, microstructure and magnetic properties of Co²⁺ and Al³⁺ substituted La-Zn nano ferrites


U. M. Mandle , L. A. Dhale, R. M. Tigote, K. S. Lohar  & B. L. Shinde  


Pages 148-160 | Received 22 Apr 2021, Accepted 04 Aug 2021, Published online: 08 Dec 2021

Cite this article  <https://doi.org/10.1080/00150193.2021.1984766> Full Article Figures & data References Citations Metrics Reprints & Permissions View PDF

Abstract

Formulae display:  **MathJax** 

Co²⁺ and Al³⁺ substituted La-Zn ferrites synthesized by sol-gel auto-combustion method with  ne as a fuel, calcination temperature of samples confirmed from TGA analysis. The observed elemental analysis (EDAX) is in good agreement with the theoretical composition. The lattice constant decreases while the crystalline size increases with the increase in concentrations of dopant. Zn²⁺ ions prefer to occupy the tetrahedron site and other ions mainly enter octahedron site. The I.R. spectra have shown two principle absorption bands near 600 and 400 cm⁻¹. SEM and TEM images reveal well defined nanoparticles with slight agglomeration. Magnetron number decreased with dopant substitution.

In this article 

1. Introduction

Ferrites are class magnetic iron oxides which plays an important role due to their extensive technological applications due to their both electrical and magnetic properties [1-3]. AB_2O_4 is a general chemical formula of spinel ferrite composed of tetrahedral-A and octahedral-B sites, where divalent- A^{2+} , trivalent- B^{3+} and oxygen ions form an fcc close packed structure. The distribution of these ions among A-sites and B-sites determines the characteristics of spinel ferrite [4].

Spinel ferrites are extensively used in applications such as sensor [5], catalysis [6, 7], biomedicine [8], MRI [9], drug delivery [10], magnetic recording [11], microwave devices [12] and magnetic ferro-fluids [13], etc. The structural, magnetic and electric properties of ferrites governed by many factors including substituents, preparation technique, elemental composition, processing temperature, particle size etc [14-16]. Numerous techniques been used for synthesis of nano-particles of ferrites are; hydrothermal [17], ball-milling [18], sol-gel auto-combustion [19], co-precipitation [15], reverse micelle [20], solid-state [21] etc. Amongst these techniques; the sol-gel auto combustion technique is facile, which is easy to control and produce the ferrite nano-particle samples with the large surface area.

Among all the spinel ferrites, Co-Zn ferrites have attracted huge attention due to its high permeability as well as high saturation magnetization. Cobalt-substituted zinc ferrites are commonly known as magnetic ceramics. The electrical and magnetic properties of ferrites extensively altered by doping of trivalent ions like Al^{3+} , Cr^{3+} etc. for Fe^{3+} ion [22, 23].

Aluminum (Al^{3+}) substituted ferrites because of their low-eddy current losses, high electrical resistivity, high squareness magnetic hysteresis loop with moderate saturation magnetization, high chemical stability are capable for numerous technological applications over broad frequency range [24, 25]. Furthermore, ferrites with good electrical and magnetic characteristics can be attained by adding rare earth (RE^{3+}) ions because of their magnetic characteristics and larger ionic radii [26]. Even, a small percentage of RE^{3+} substitution can alter the magnetic and electrical properties of ferrites [27].

to 0.5 in steps of 0.1) synthesized by sol-gel auto-combustion method.

2. Materials and method

Nanocrystalline Co²⁺ and Al³⁺ substituted La-Zn ferrites, with composition of La_{0.1}Co_xZn_{1.0-x}Fe_{1.9-y}Al_yO₄ were synthesized by the sol-gel auto-combustion method [6, 19] corresponding from analytical grade reagent having purity 99%, those were Lanthanum nitrate [La(NO₃)₃·6H₂O], Cobalt nitrate [Co(NO₃)₂·6H₂O], Zinc nitrate [Zn(NO₃)₂·6H₂O], Aluminum Nitrate [Cr(NO₃)₃·6H₂O], Ferric nitrate [Fe(NO₃)₃·9H₂O] and 97% Glycine [NH₂-CH₂-COOH], were used in the synthesis without any further treatment. All nitrates were dissolved in distilled water to obtain a mixed solution in desired composition. The reaction procedure was carried out in an air atmosphere without the protection of inert gases. The molar ratio of metal nitrates to glycine was 1:3. The metal nitrates were dissolved together in the minimum amount of double-distilled water required to obtain a clear solution. An aqueous solution of glycine was mixed with the metal-nitrate solution and pH ≈ 7 of reaction mixture was maintained by gradually addition of the ammonia solution. The mixed solution was kept on a hot plate with constant stirring at 90 °C. A viscous brown gel was formed as a result of evaporation of solution. When all of the water molecules were evaporated; the viscous gel obtained and it began to froth, after few a minute, the gel self ignited and burnt with glowing flints. The auto-combustion completed within a short time, yielding brown colored ashes referred as the precursor.

The thermal analysis of synthesized precursors was performed using TGA/DSC Thermal analyzer SDT Q 600 V20.9 Build 20, by heating precursors from room temperature to 800 °C with a heating rate 10 °C per minutes in air atmosphere. The crystallographic structures were identified by X-ray powder diffraction with Cu K α radiation ($\lambda = 1.5405 \text{ \AA}$) by Phillips X-ray diffractometer (Model 3710). Morphology and structure of the samples were studied on JEOL-JSM-5600 N scanning electron microscope (SEM) and on Philips (model CM 200) transmission electron microscope (TEM). The elemental composition determined by energy dispersive x-ray analysis (EDAX, Inca Oxford, attached to the SEM). The infrared spectra of all the samples were recorded at room temperature in the range 200 to 800 cm⁻¹ using Perkin Elmer infrared spectrophotometer. The magnetic measurements were performed at room temperature using a commercial PARC FG&G VSM 4500 vibrating sample magnetometer.

In this article


^

3. Result and discussion

3.1. TGA/DTA analysis

The typical decomposition pattern of Co²⁺ and Al³⁺ substituted La-Zn ferrites ($x = y = 0.2$) precursor is shown in Figure 1, indicate the first endothermic peak is observed due to loss of coordinated water molecule. Above temperature 350 °C there is mass loss which may be related to solid state an exothermic reaction results in formation of ferro-spinel compounds. The other precursors of series show similar type of decomposition patterns and convert in to ferrites in the temperature around 450 °C. Finally all precursors were calcinated at 450 °C for 4 hours to get desired nano ferro- spinels.

Figure 1. Typical TGA/DTA plot of La_{0.1}Co_xZn_{1.0-x}Fe_{1.9-y}Al_yO₄ ($x = y = 0.2$).

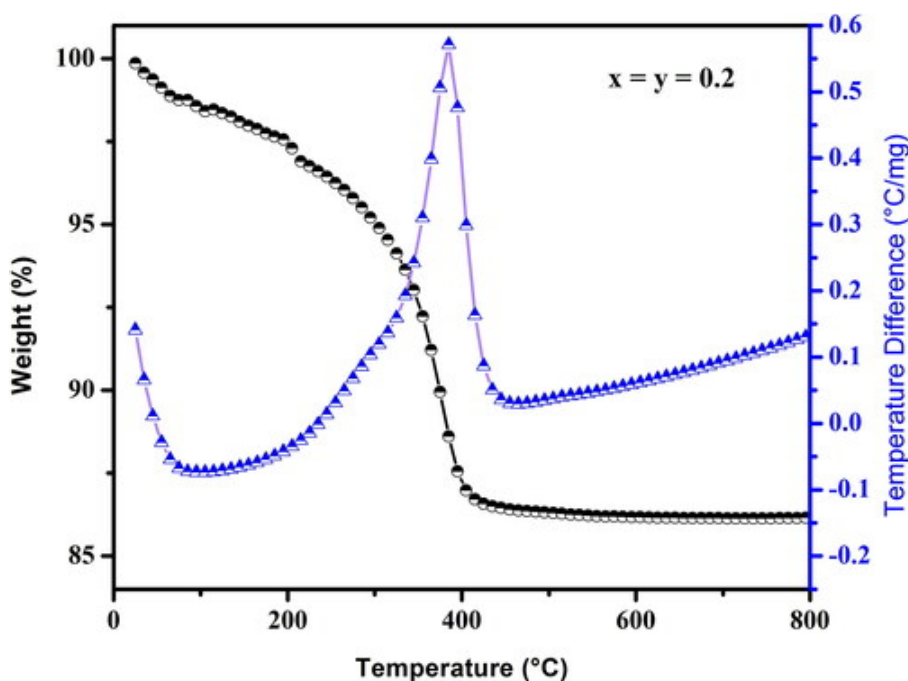

Display full size

3.2. Elemental analysis


Energy dispersive X-ray analysis (EDAX) was obtained to investigate the elemental stoichiometric composition of the prepared La-Zn ferrite samples with Co²⁺ and Al³⁺ substitutions. EDAX of a typical samples ($x = y = 0.2$ and 0.4) are shown in by Figure 2a and 2b respectively. The theoretical and observed atomic elemental compositions are graphically illustrated in Figure 3.

In this article

^


compositions used for the preparation.

Figure 2. (a) Typical EDAX pattern of $\text{La}_{0.1}\text{Co}_x\text{Zn}_{1.0-x}\text{Fe}_{1.9-y}\text{Al}_y\text{O}_4$ ($x = y = 0.2$). (b) Typical EDAX pattern of $\text{La}_{0.1}\text{Co}_x\text{Zn}_{1.0-x}\text{Fe}_{1.9-y}\text{Al}_y\text{O}_4$ ($x = y = 0.4$).

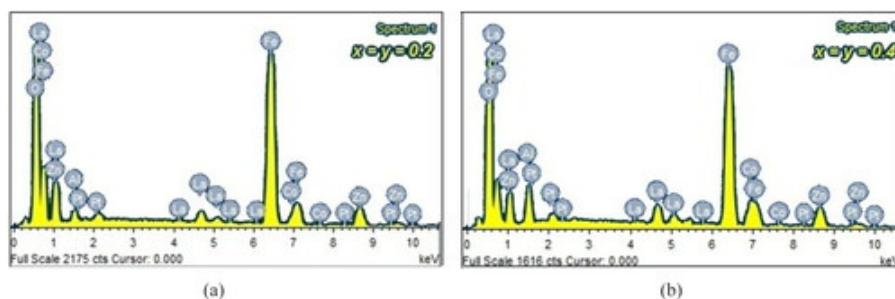

Display full size

Figure 3. Plots of Observed and Theoretical elemental % versus composition ($x = y$).

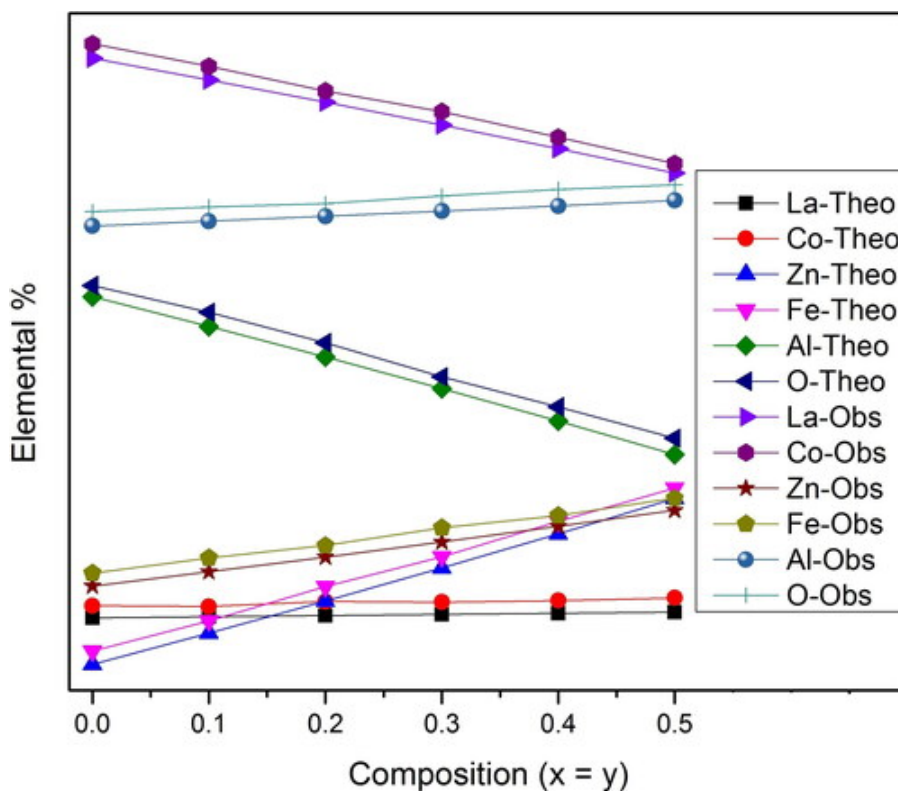

Display full size

3.3. Structural analysis


The XRD patterns of calcinated samples is shown in Figure 4. The XRD patterns showed the appropriate peaks to the Co²⁺ and Al³⁺ substituted La-Zn ferrites and with some secondary

In this article

^

(JCPDS # 75-0541) [28].

Figure 4. XRD patterns of La_{0.1}Co_xZn_{1.0-x}Fe_{1.9-y}Al_yO₄ (x = y = 0.0 to 0.5).

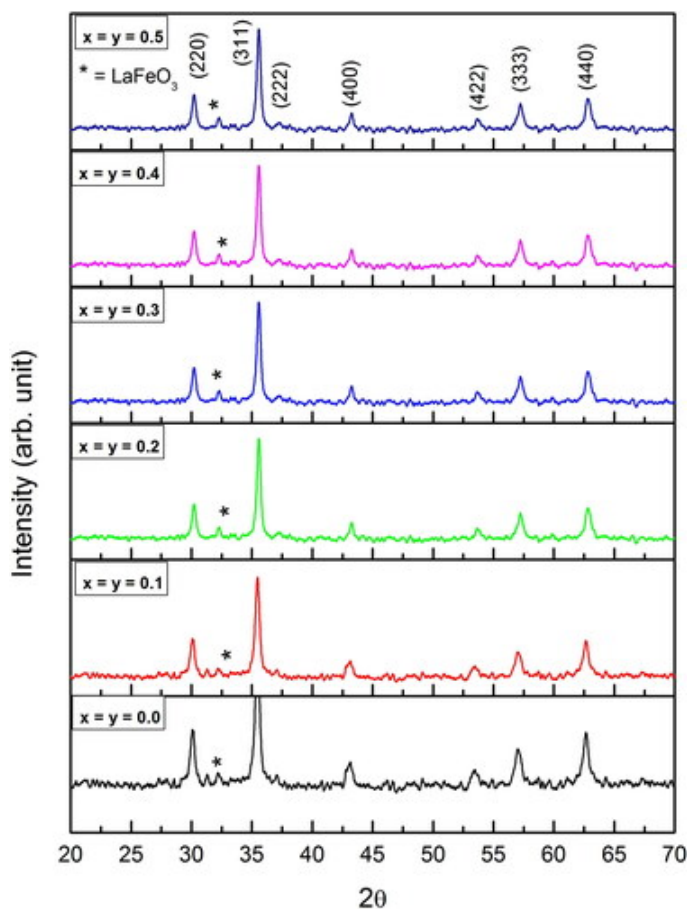

Display full size

The lattice constant 'a' was calculated by using Eq. (1) [29],

$$a = d\sqrt{N}$$

1) Where, 'a' is lattice constant, 'd' is interplaner spacing and $\sqrt{N} = \sqrt{(h^2 + k^2 + l^2)}$. The lattice constant 'a' decreased from 8.4388 Å to 8.3226 Å with the Co²⁺ and Al³⁺ ions substitution to the La-Zn ferrite system (Table 1), which is related to the ionic radii of respective ions in the composition where smaller Co²⁺ (0.65 Å) ions was substituted for the larger Zn²⁺ (0.74 Å) ions [30] and smaller Al³⁺ (0.50 Å) substituted for the larger Fe³⁺ (0.67 Å) ions [15].

Table 1. Lattice parameter 'a', X-ray density 'd_x', particle size 'D_{XRD}',

In this article



Download CSV Display Table

The X-ray density ' d_x ' was obtained by using the following relation:

$$d_x = \frac{nM}{N_A V}$$

2) Where, d_x = X-ray density, n = Number of molecules per unit volume (8 for cubic structure), M = Molecular weight of the composition, N_A = Avogadro's number = 6.02214×10^{23} and V = Volume = a^3 . X-ray density decreased with Co²⁺ and Al³⁺ substitution from 5.5121 to 5.3392 g/cm³ (Table 1).

The broad diffraction peaks exhibit the fine particle nature of synthesized ferrite samples. The average crystalline size ' D_{XRD} ' of the prepared samples was determined from the most intense peak (311) plane of XRD and by using following Scherer relation [31].

$$D_{XRD} = \frac{k\lambda}{\beta \cos \theta_B}$$

3) Where, D = Particle Size, k = Constant (0.94), λ = Wavelength of incident X-rays, β = Full Width of Half Maxima (FWHM in radians) or broadening of the diffraction peak and θ_B = Bragg's angle. The calculated crystalline size are of the order few nm and is tabulated in Table 1. The crystalline size decreased from 23.994 to 14.448 nm with the Co²⁺ and Al³⁺ substitution.

The hopping lengths of A and B-sites (L_A and L_B , respectively) among the magnetic ions are obtained through the equation discussed elsewhere [32],

$$L_A = \frac{a\sqrt{3}}{4}$$

4)

$$L_B = \frac{a\sqrt{2}}{4}$$

5) Where, ' a ' is lattice constant.

It has been illustrated from Table 1 that the hopping lengths (L_A and L_B) decreased with increasing Co²⁺ and Al³⁺ concentration. The decrease in both the hopping lengths with

aluminum ions that occupy the B-sites will cause an increase in both A–A and A–B interactions and will reduce the B–B interaction. This can be ascribed to the transfer of Fe ions from B-sites to A-sites due to the insertion of both Co²⁺ and Al³⁺ ions to the B-sites. Moreover, the increase of Co²⁺ ions in the composition due to increase of x is associated with a decrease of Zn²⁺ ions. The Al³⁺ substitution to the Fe³⁺ ion difference between ionic radii of the substituted ions that brought the magnetic ions closer to each other with the decrease in hopping lengths [25].

3.4. Cation distribution

The cation distribution of the available tetrahedral and octahedral sites in spinel ferrite composition was obtained (Table 2) through the analysis of the X-ray diffraction patterns where the Bertaut method [33].

Table 2. Cation distribution over tetrahedral A and octahedral B sites and Ionic radii of tetrahedral A-site (r_A), octahedral B-site (r_B), theoretical lattice constant (a_{th}) and oxygen positional parameter (u).



Download CSV Display Table

The Zn²⁺ ions showed preference to occupy the tetrahedral A sub lattice and La³⁺, Co²⁺, Al³⁺ ions mainly go into octahedron B sub lattice [34]. However, Fe³⁺ ions occupied both the available A and B sub lattices. Higher fraction of Co²⁺ ions occupied the B-site due to their tendency for large octahedral site energy. The fraction Co²⁺ ions at B-site increased at the cost of Fe³⁺ ions with the substitution of Co²⁺ ions. The Al³⁺ replaced the Fe³⁺ from B-sites due to their preference to the B-site and favorable crystal field effects [35]. The percentage of Al³⁺ ions whereas the fraction of Fe³⁺ ions in B-sites decreased linearly with the increasing Al³⁺ content. The ionic radii of the constituent ions such as Al³⁺ (0.50 Å), Zn²⁺ (0.81 Å), Co²⁺ (0.72 Å) and Fe³⁺ (0.67 Å) may also govern the site occupancies in spinel ferrite system [36].

The oxygen positional parameters (u), experimental lattice constants (a_{exp}), the relative intensities of experimental and calculated XRD peaks (I_{hkl}) and cation distribution for each composition are tabulated in Table 3. The mean ionic radius of the A and B-sites (r_A and r_B respectively) was obtained through the relations discussed elsewhere [37]. It is observed that

Co²⁺ concentration (Table 3). The increase in r_B is related to the occupancy of B site by the smaller Co²⁺ (0.72 Å) ions that replaced Zn²⁺ (0.74 Å) ions [38].

Table 3. Band position (ν_1 and ν_2), force constants K_0 , K_t and bond lengths R_A , R_B .




Download CSV Display Table

3.5. Infrared spectroscopy

IR spectra for all the synthesized ferrite samples are showed in Figure 5. The spectrum showed two major absorption bands (ν_1 and ν_2) which is an important characteristic of all the ferrites, near 600 and 400 cm^{-1} (Table 3). The high frequency band (ν_1) is allocated to the intrinsic lattice vibration of the tetrahedral sites of $\text{Fe}^{3+}\text{-O}^{2-}$. On the other hand, the lower frequency band (ν_2) is ascribed to the stretching vibration of octahedral complexes [39]. The calculated values bond lengths for A-site (R_A) and B-site (R_B) are listed in Table 4. The bond lengths R_A and R_B decreased with Co²⁺ and Al³⁺ substitution. The force constants K_t and K_0 increased with the Co²⁺ and Al³⁺ substitution.

Figure 5. IR spectrum of $\text{La}_{0.1}\text{Co}_x\text{Zn}_{1.0-x}\text{Fe}_{1.9-y}\text{Al}_y\text{O}_4$ ($x = y = 0.0$ to 0.5).

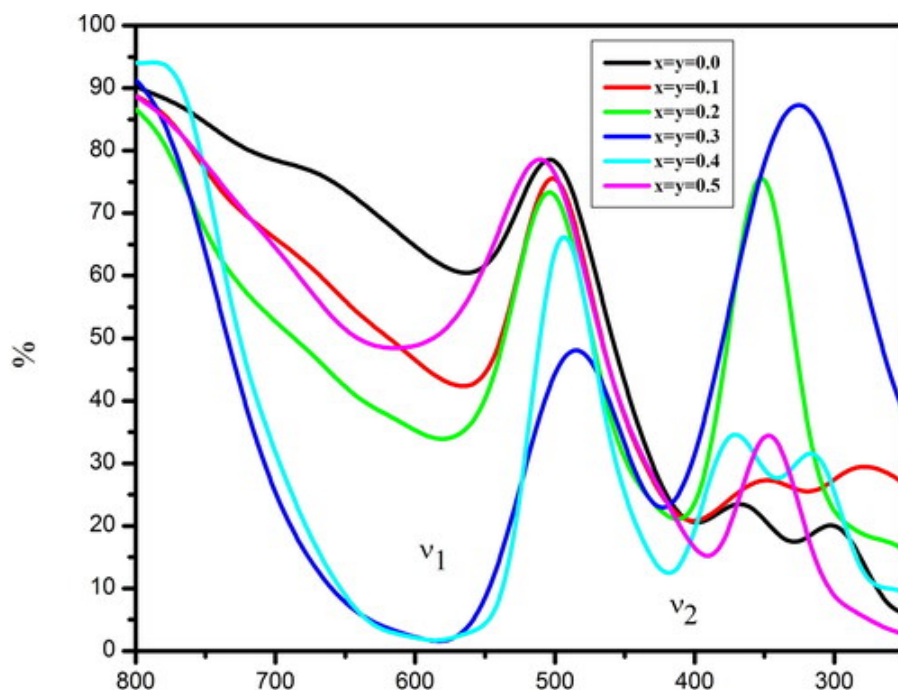

In this article



[Display full size](#)

Table 4. Values of molecular weight, saturation magnetization, Remnant magnetization, coercivity and magneton number.




[Download CSV](#) [Display Table](#)

3.6. Scanning electron microscopy

Typical SEM micrograph of the prepared ferrites ($x = y = 0.0$) shown in [Figure 6](#). SEM images indicate formation of well defined nanoparticles with slight agglomeration of the sample with inhomogeneous broader grain size distribution. It is observed from SEM images that the morphology was affected by the Co²⁺ and Al³⁺ substitutions. The SEM images showed the amorphous and porous in nature of the prepared samples. The reduction in the grain size and increment in porosity is observed with the Co²⁺ and Al³⁺ substitutions. Such observations suggested that the substitution of Co²⁺ and Al³⁺ in La-Zn ferrite during sol-gel combustion process enabled a better homogeneous in the samples and, thus, a more precise microstructure is attained.


Figure 6. Typical scanning electron micrographs of La_{0.1}Co_xZn_{1.0-x}Fe_{1.9-y}Al_yO₄ ($x = y = 0.0$).

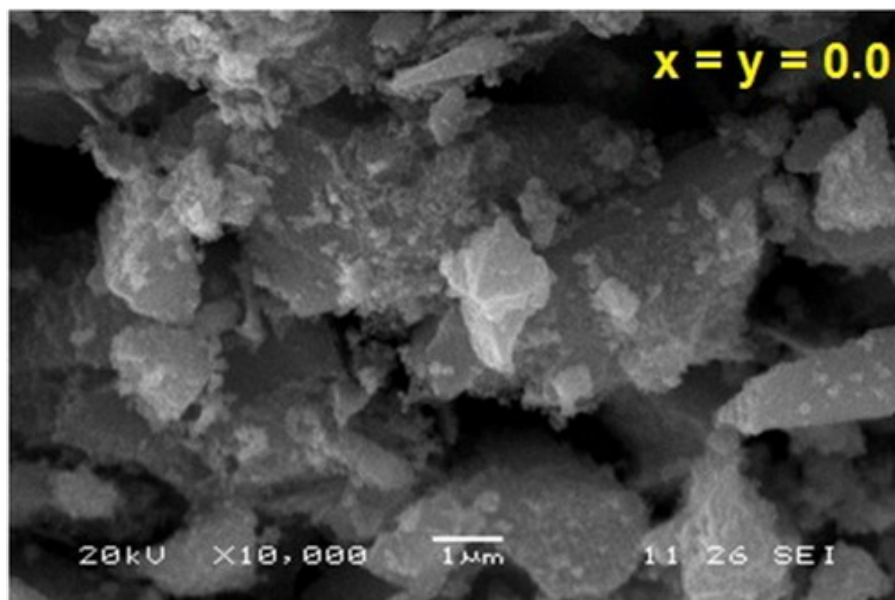[Display full size](#)[In this article](#)

3.7. Transmission electron microscopy


Figure 7 shows the typical TEM image and their respective histogram (Figure 8) of the sample ($x = y = 0.0$). The values of the particle size obtained from TEM analysis are around 24–16 nm and these values are good agreements with the values are determined from XRD. Most of the spherical shaped nanoparticles has been observed, at the same time, few elongated shaped agglomerated nano-particles were also evidenced due to magnetic interaction among the particles.

Figure 7. Typical transmission electron micrograph of $\text{La}_{0.1}\text{Co}_x\text{Zn}_{1.0-x}\text{Fe}_{1.9-y}\text{Al}_y\text{O}_4$ ($x = y = 0.0$).

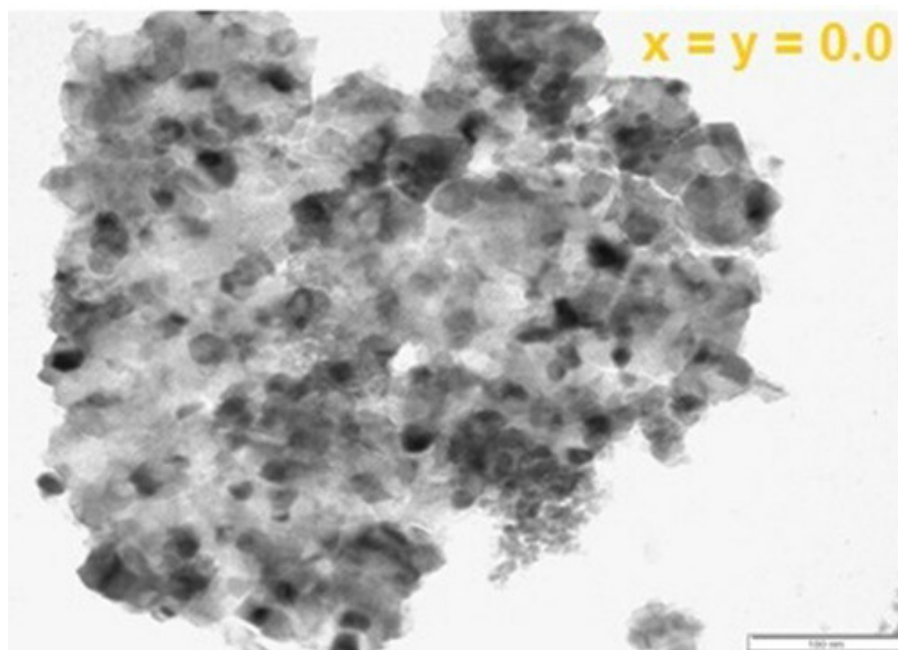

[Display full size](#)


Figure 8. Particle size distribution graph of $\text{La}_{0.1}\text{Co}_x\text{Zn}_{1.0-x}\text{Fe}_{1.9-y}\text{Al}_y\text{O}_4$ ($x = y = 0.0$).

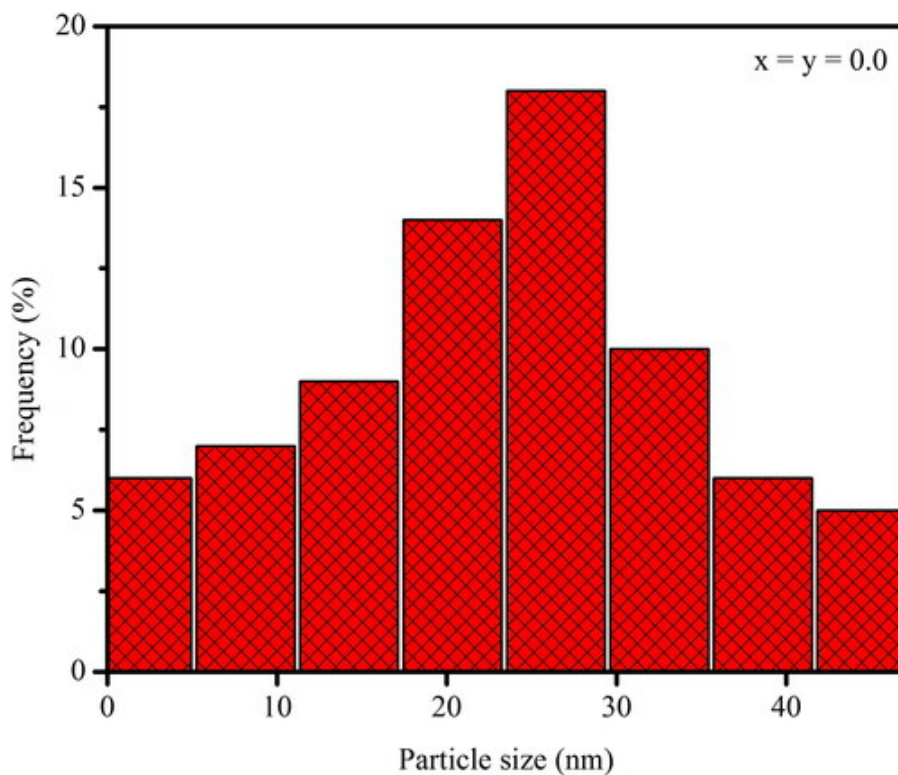

Display full size

Figure 9 showed typical selected area electron diffraction (SAED) pattern of the ($x = y = 0.0$) sample. The Debye ring pattern with superimposition of the bright spot indicates polycrystalline nature of the prepared sample [31].

Figure 9. SAED pattern of $\text{La}_{0.1}\text{Co}_x\text{Zn}_{1.0-x}\text{Fe}_{1.9-y}\text{Al}_y\text{O}_4$ ($x = y = 0.0$).

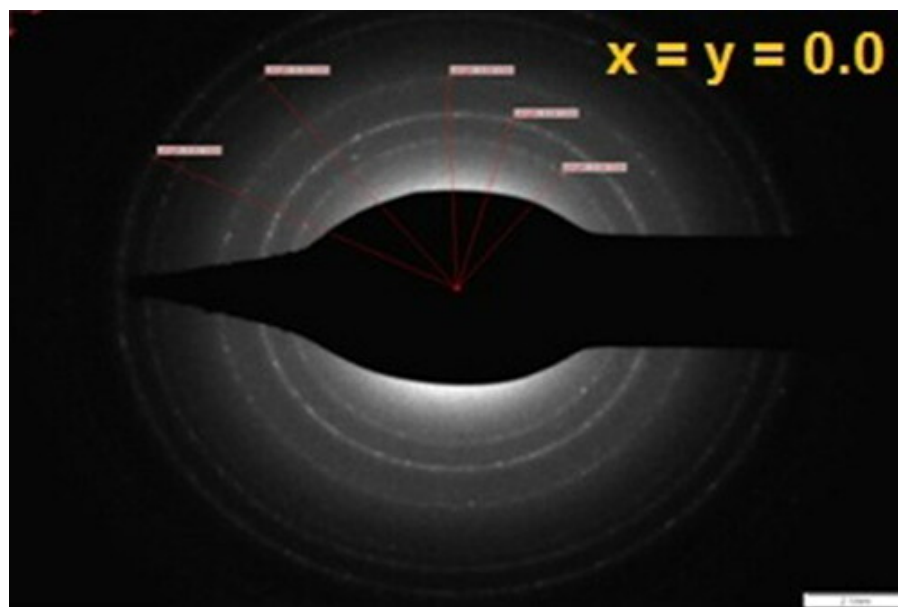

Display full size

In this article




3.8. Magnetization

Magnetic properties of ferrites are sensitively dependent on the structure, composition, defects, crystallite size; internal strain and cation distribution [40]. Neel's two sub-lattice models are applied to understand the magnetic behavior of the samples. According to Neel's two sub-lattice Model of ferrimagnetism Neel's magnetic moment n_B is given by equation [41]. The super-exchange interactions of these samples strongly depend on the distribution of the cations on the tetrahedral, A- and the octahedral, B-site.

It is observed from Fig. 9, that saturation magnetization decreases up to certain applied field above which saturation magnetization remains almost constant. Saturation magnetization (M_s), coercivity (H_c), and magneton number (n_B) derived from hysteresis loops and are given in Table 4. Saturation magnetization decreases from 36.546 emu/g to 3.397 emu/g, with increase in Co²⁺ and Al³⁺ content. Remnant magnetization (M_r) obtained from the hysteresis loop is observed to decreased with the increase in Co²⁺ and Al³⁺ substitution. The increases in coercivity could also be related to the higher magneto crystalline anisotropy of Co²⁺ ions as compared to the Fe³⁺ ions.

It is illustrated in Figure 10, that saturation magnetization (M_s) increased up to specific applied magnetic field above which M_s attains a saturated moment. M_s , coercivity (H_c), and magneton number (n_B) was derived from hysteresis loops and are tabulated in Table 4. Saturation magnetization decreases from 32.3102 emu/g to 12.0344 emu/g, with increase in Co²⁺ and Al³⁺ content. Remnant magnetization (M_r) observed from the hysteresis loop is decreased with the Co²⁺ and Al³⁺ substitution. The increase in coercivity should be related to the higher magneto crystalline anisotropy of Co²⁺ ions as compared to the Fe³⁺ ions.

Figure 10. Hysteresis loops of La_{0.1}Co_xZn_{1.0-x}Fe_{1.9-y}Al_yO₄ ($x = y = 0.0$ to 0.5).

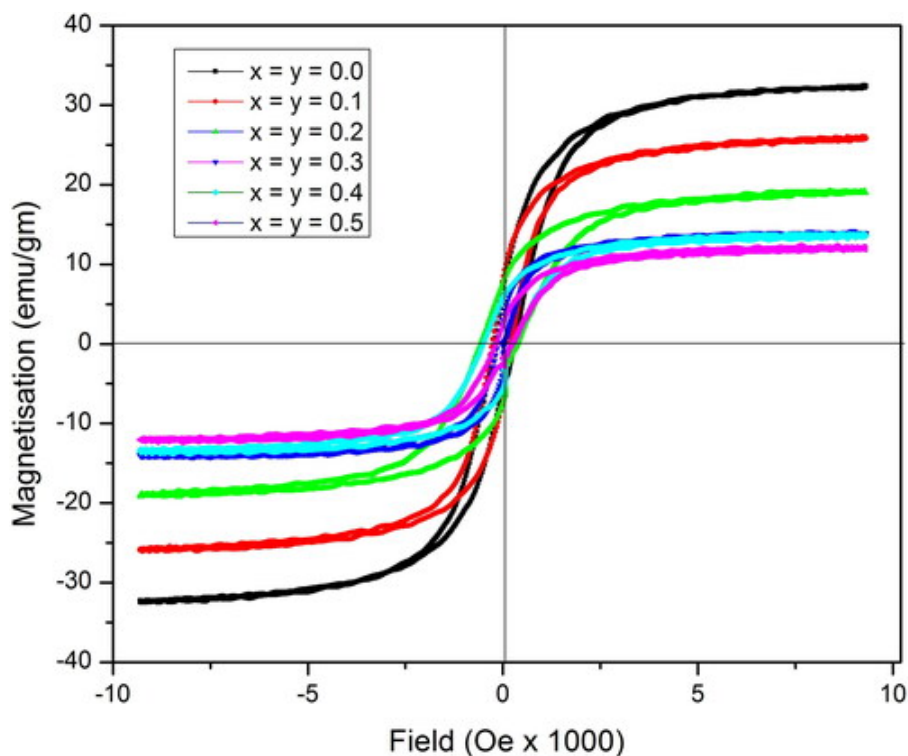

Display full size

The observed magneton number n_B (the Ms per formula unit in μ_B) was determined by hysteresis loops. The net magnetic moment ($n_B \text{ Cal.}$) can be obtained from the sum of the magnetic moments at A and B sub lattices, i.e., $n_B \text{ Cal.} = M_B - M_A$; where, M_B and M_A are the B and A sub-lattice magnetic moments in μ_B . The $n_B \text{ Cal.}$ were obtained through cation distribution and magnetic moments of Fe^{3+} ($5.92\mu_B$), Al^{3+} ($0\mu_B$), Zn^{2+} ($0\mu_B$), Co^{2+} ($3.88\mu_B$) and La^{3+} ($3.58\mu_B$). Magneton number decreased with Co^{2+} and Al^{3+} substitution (Table 4).

4. Conclusions

Nanocrystalline ferrites, with composition $\text{La}_{0.1}\text{Co}_x\text{Zn}_{1-x}\text{Fe}_{1.9-y}\text{Al}_y\text{O}_4$ in step of $x = y = 0.1, 0.2, 0.3, 0.4$ and 0.5 were successfully prepared by the sol-gel auto-combustion method. All precursors were calcined at 450°C for four hour. The observed elemental analysis from EDAX is in good agreement with the theoretical values. The lattice constant decreased from 8.4388 \AA to 8.3226 \AA , and the crystalline size decreased from 23.994 nm to 14.448 nm with the Co^{2+} and Al^{3+} ions substitution. Zn^{2+} ions prefer to occupy the tetrahedron site (A sub lattice) and both La^{3+} , Co^{2+} , Al^{3+} ions mainly enter octahedron site (B sub lattice). The I.R. spectra showed two principle

In this article

^

ferrites and supported the XRD investigations. SEM and TEM images revealed well defined nanoparticles with slight agglomeration. Magnet number decreased with Co²⁺ and Al³⁺ substitution.

References

1. R. Jasrotia et al., Synthesis and characterization of Mg-Ag-Mn nano-ferrites for electromagnet applications, *Phys. B Condens. Matter.* **569**, 1 (2019). DOI: <https://doi.org/10.1016/j.physb.2019.05.033>.
| [Web of Science ®](#) | [Google Scholar](#)
2. K. K. Kefeni, B. B. Mamba, and T. A. Msagati, Application of spinel ferrite nanoparticles in water and wastewater treatment: a review, *Sep. Purif. Technol.* **188**, 399 (2017). DOI: <https://doi.org/10.1016/j.seppur.2017.07.015>.
| [Web of Science ®](#) | [Google Scholar](#)
3. K. A. Ganure et al., Synthesis, structural and magnetic properties of Ni²⁺ and In³⁺ doped cobalt ferrite and application as catalyst for synthesis of Bis-(Indolyl) methane derivatives, *Mater. Today: Proc.* (2021). DOI: <https://doi.org/10.1016/j.matpr.2021.02.327>.
| [Google Scholar](#)
4. C. A. P. Gómez et al., Structural parameters and cation distributions in solid state synthesized Ni-Zn ferrites, *Mater. Sci. Eng. B.* **236**, 48 (2018). DOI: <https://doi.org/10.1016/j.mseb.2018.12.003>.
| [Web of Science ®](#) | [Google Scholar](#)
5. H. Yang et al., A simple gas sensor based on zinc ferrite hollow spheres: Highly sensitivity, excellent selectivity and long-term stability, *Sens. Actuators, B.* **280**, 34 (2019). DOI: <https://doi.org/10.1016/j.snb.2018.10.056>.

6. U. M. Mandle et al., An efficient one pot multicomponent synthesis of pyrano pyrazoles using Cu²⁺ doped Ni-Zn nano ferrite catalyst, *Mater. Today: Proc.* **46**, 6122 (2021), DOI: <https://doi.org/10.1016/j.matpr.2020.03.583>.
| [Google Scholar](#)
7. T. Rahman, G. Borah, and P. K. Gogoi, Spinel structured copper ferrite nano catalyst with magnetic recyclability for oxidative decarboxylation of phenyl acetic acids, *Catal. Lett.* **150** (8), 2267 (2020). DOI: <https://doi.org/10.1007/s10562-020-03131-0>.
| [Web of Science ®](#) | [Google Scholar](#)
8. N. L. Martínez-Rodríguez et al., In vitro toxicity assessment of zinc and nickel ferrite nanoparticles in human erythrocytes and peripheral blood mononuclear cell, *Toxicol. In Vitro* **57**, 54 (2019). DOI: <https://doi.org/10.1016/j.tiv.2019.02.011>.
| [PubMed](#) | [Web of Science ®](#) | [Google Scholar](#)
9. Y. Du et al., Optimization and design of magnetic ferrite nanoparticles with uniform tumor distribution for highly sensitive MRI/MPI performance and improved magnetic hyperthermia therapy, *Nano Lett.* **19** (6), 3618 (2019). DOI: <https://doi.org/10.1021/acs.nanolett.9b00630>.
| [PubMed](#) | [Web of Science ®](#) | [Google Scholar](#)
10. A. Nigam, and S. J. Pawar, Structural, magnetic, and antimicrobial properties of zinc doped magnesium ferrite for drug delivery applications, *Ceram. Int.* **46** (4), 4058 (2020). DOI: <https://doi.org/10.1016/j.ceramint.2019.10.243>.
| [Web of Science ®](#) | [Google Scholar](#)
11. V. K. Chakradhary, A. Ansari, and M. J. Akhtar, Design, synthesis, and testing of high coercivity cobalt doped nickel ferrite nanoparticles for magnetic applications, *J. Magn. Magn.* **469**, 674 (2019). DOI: <https://doi.org/10.1016/j.jmmm.2018.09.021>.
| [Web of Science ®](#) | [Google Scholar](#)
12. I. H. Hasan et al., Nickel zinc ferrite thick film with linseed oil as organic vehicle for microwave device applications, *Mater. Chem. Phys.* **236**, 121700 (2020). DOI: <https://doi.org/10.1016/j.materchemphys.2020.121700>.

| [Web of Science®](#) | [Google Scholar](#)

13. W. I. Liu et al., Impact of oscillating magnetic field on the thermal-conductivity of water-Fe₃O₄ and water-Fe₃O₄/CNT ferro-fluids: experimental study, *J. Magn. Magn.* **484**, 258 (2019). DOI: <https://doi.org/10.1016/j.jmmm.2019.04.042>.

| [Web of Science®](#) | [Google Scholar](#)

14. G. S. Kumar, and A. R. Synthesis, structural, dielectric and magnetic properties of spinel structure of Ca²⁺ substitute in Cobalt ferrites (Co_{1-x}Ca_xFe₂O₄), *Chin. J. Phys.* **56** (3), 1262 (2018). DOI: <https://doi.org/10.1016/j.cjph.2018.02.014>.

| [Web of Science®](#) | [Google Scholar](#)

15. B. L. Shinde et al., Synthesis and characterization of Al³⁺ substituted Ni-Cu-Zn nano ferrites, *J. Therm. Anal. Calorim.* (2021). DOI: <https://doi.org/10.1007/s10973-021-10719-0>.

| [Google Scholar](#)

16. K. Jalaiah, and K. V. Babu, Structural, magnetic and electrical properties of nickel doped Mn-Zn spinel ferrite synthesized by sol-gel method, *J. Magn. Magn.* **423**, 275 (2017). DOI: <https://doi.org/10.1016/j.jmmm.2016.09.114>.

| [Web of Science®](#) | [Google Scholar](#)

17. M. Li et al., Synthesis and characterization of nanosized MnZn ferrites via a modified hydrothermal method, *J. Magn. Magn.* **439**, 228 (2017). DOI: <https://doi.org/10.1016/j.jmmm.2017.04.015>.

| [Web of Science®](#) | [Google Scholar](#)

18. W. Chen et al., Structural and magnetic properties evolution of Co-Nd substituted M-type hexagonal strontium ferrites synthesized by ball-milling-assisted ceramic process, *J. Elect. Mater.* **47** (3), 2110 (2018). DOI: <https://doi.org/10.1007/s11664-017-6021-8>.

| [Web of Science®](#) | [Google Scholar](#)

ferrites, *Acta Chim Slov.* **64** (4), 931 (2017). DOI: <https://doi.org/10.17344/acsi.2017.3619>.

| [PubMed](#) | [Web of Science®](#) | [Google Scholar](#)

20. M. Hashim et al., Manganese ferrite prepared using reverse micelle process: structural and magnetic properties characterization, *J. Alloys Compd.* **642**, 70 (2015). DOI: <https://doi.org/10.1016/j.jallcom.2015.04.085>.

| [Web of Science®](#) | [Google Scholar](#)

21. M. K. Anupama, B. Rudraswamy, and N. Dhananjaya, Influence of trivalent (Gd³⁺, Cr³⁺) ion substitution on the structural and magnetic properties of Ni_{0.4}Zn_{0.6}Cr_{0.5}GdxFe_{1.5-x}O₄ ferrite nanoparticles, *IJNT* **14** (9/10/11), 867 (2017). DOI: <https://doi.org/10.1504/IJNT.2017.086770>.

| [Google Scholar](#)

22. M. Z. Khan et al., Comprehensive study on structural, electrical, magnetic and photocatalytic degradation properties of Al³⁺ ions substituted nickel ferrites nanoparticles, *J. Alloys Compd.* **848**, 155795 (2020). DOI: <https://doi.org/10.1016/j.jallcom.2020.155795>.

| [Web of Science®](#) | [Google Scholar](#)

23. V. K. Mande et al., Effect of Zn²⁺-Cr³⁺ substitution on structural, morphological, magnetic and electrical properties of NiFe₂O₄ ferrite nanoparticles, *J. Mater. Sci: Mater. Electron.* **29** (17), 15259 (2018). DOI: <https://doi.org/10.1007/s10854-018-9668-x>.

| [Web of Science®](#) | [Google Scholar](#)

24. T. K. Bromho et al., Understanding the impacts of Al³⁺-substitutions on the enhancement of magnetic, dielectric and electrical behaviors of ceramic processed nickel-zinc mixed ferrites: FTIR assisted studies, *Mater. Res. Bull.* **97**, 444 (2018). DOI: <https://doi.org/10.1016/j.materresbull.2017.09.013>.

| [Web of Science®](#) | [Google Scholar](#)

25. H. M. Zaki, S. H. Al-Heniti, and M. M. Aljwiher, Synthesis, structural, magnetic and dielectric studies of aluminum substituted cobalt-zinc ferrite, *Physica B: Condens. Matter* **507**

In this article



| [Web of Science®](#) | [Google Scholar](#)

26. K. L. Routray, S. Saha, and D. Behera, Rare-earth (La³⁺) substitution induced changes in the structural, dielectric and magnetic properties of nano-CoFe₂O₄ for high-frequency and magneto-recording devices, *Appl. Phys. A.* **125** (5), 1 (2019). DOI: <https://doi.org/10.1007/s00339-019-2615-8>.

| [Web of Science®](#) | [Google Scholar](#)

27. S. M. Kabbur et al., Magnetic interactions and electrical properties of Tb³⁺ substituted NiCuZn ferrites, *J. Magn. Magn.* **473**, 99 (2019). DOI: <https://doi.org/10.1016/j.jmmm.2018.10.041>.

| [Web of Science®](#) | [Google Scholar](#)

28. K. A. Ganure et al., Influence of La³⁺ doped nano spinel ferrites on infrared spectroscopy in elastic properties via O/W micro emulsion method, *Ferroelectrics* **573** (1), 236 (2021). DOI: <https://doi.org/10.1080/00150193.2021.1890480>.

| [Web of Science®](#) | [Google Scholar](#)

29. S. G. Gawas, and V. M. S. Verenkar, Precursor combustion synthesis of nanocrystalline cobalt substituted nickel zinc ferrites from hydrazinated mixed metal fumarates, *Thermochim. Acta* **605**, 16 (2015). DOI: <https://doi.org/10.1016/j.tca.2015.02.010>.

| [Web of Science®](#) | [Google Scholar](#)

30. T. R. Tatarchuk et al., Structural characterization and antistructure modeling of cobalt-substituted zinc ferrites, *J. Alloys Compd.* **694**, 777 (2017). DOI: <https://doi.org/10.1016/j.jallcom.2016.10.067>.

| [Web of Science®](#) | [Google Scholar](#)

31. B. D. Cullity, *Elements of X-Ray Diffraction* (Addison-Wesley Publ. Comp. Inc., Reading, MA, 1956), p. 99.

[Google Scholar](#)

powder: Physical and magnetic interactions, *Powder Technol.* **259**, 14 (2014). DOI: <https://doi.org/10.1016/j.powtec.2014.03.053>.

| [Web of Science®](#) | [Google Scholar](#)

33. L. Weil, F. Bertaut, and L. Bochirol, Propriétés magnétiques et structure de la phase quadratique du ferrite de cuivre, *J. Phys. Radium* **11** (5), 208 (1950). DOI: <https://doi.org/10.1051/jphysrad:01950001105020800>.

| [Web of Science®](#) | [Google Scholar](#)

34. M. Han, C. R. Vestal, and Z. J. Zhang, Quantum couplings and magnetic properties of CoCr_xFe_{2-x}O₄ (0 < x < 1) spinel ferrite nanoparticles synthesized with reverse micelle method, *J. Phys. Chem. B.* **108**, 583 (2004). DOI: <https://doi.org/10.1021/jp035966m>.

| [Web of Science®](#) | [Google Scholar](#)

35. H. M. Widatallah et al., On the synthesis and cation distribution of aluminum-substituted spinel-related lithium ferrite, *Mater. Lett.* **59** (8–9), 1105 (2005). DOI: <https://doi.org/10.1016/j.matlet.2004.12.017>.

| [Web of Science®](#) | [Google Scholar](#)

36. L. Vegard, The constitution of the solid solution and the space filling of the atoms, *Z. Physik.* **5** (1), 17 (1921). DOI: <https://doi.org/10.1007/BF01349680>.

| [Google Scholar](#)

37. K. J. Standley, *Oxide Magnetic Materials* (Oxford University Press, Oxford, UK, 1972).

[Google Scholar](#)

38. U. B. Shinde et al., Preparation and characterization of Co²⁺ substituted Li–Dy ferrite ceramics, *Ceram. Int.* **39** (5), 5227 (2013). DOI: <https://doi.org/10.1016/j.ceramint.2012.12.022>.

| [Web of Science®](#) | [Google Scholar](#)

39. R. D. Waldron, Preparation of magnetic nanoparticles, *Phys. Rev.* **99** (6), 1727 (1955). DOI:

<https://doi.org/10.1103/PhysRev.99.1727>

In this article



[Web of Science®](#) | [Google Scholar](#)

40. L. Z. Li et al., Structural and magnetic properties of Cr-substituted NiZnCo ferrite nanopowders, *J. Magn. Magn.* **381**, 328 (2015). DOI: <https://doi.org/10.1016/j.jmmm.2015.01.020>.

[Web of Science®](#) | [Google Scholar](#)

41. L. Néel, Propriétés magnétiques des ferrites; ferrimagnétisme et antiferromagnétisme, *Ann. Phys.* **12** (3), 137 (1948). DOI: <https://doi.org/10.1051/anphys/194812030137>.

[Google Scholar](#)

[Download PDF](#)

Related research

[People also read](#)



[Recommended articles](#)

[Cited by](#)

1

In this article



Information for

- Authors
- R&D professionals
- Editors
- Librarians
- Societies

Opportunities

- Reprints and e-prints
- Advertising solutions
- Accelerated publication
- Corporate access solutions

Open access

- Overview
- Open journals
- Open Select
- Dove Medical Press
- F1000Research

Help and information

- Help and contact
- Newsroom
- All journals
- Books

Keep up to date

Register to receive personalised research and resources by email



Sign me up



Copyright © 2024 Informa UK Limited [Privacy policy](#) [Cookies](#) [Terms & conditions](#)



[Accessibility](#)

Registered in England & Wales No. 3099067
5 Howick Place | London | SW1P 1WG

In this article

